
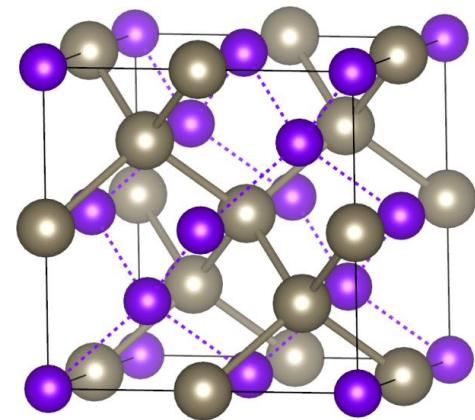


Lecture 10:


Main group compounds

- Some general trends and classifications for non-molecular main group compounds
- Allotropes
 - Group 14 elements
 - Group 15 elements
 - Group 16 elements
- Zintl phases
 - General principles
 - Typical examples
 - Zintl ions
 - Semiconducting clathrates

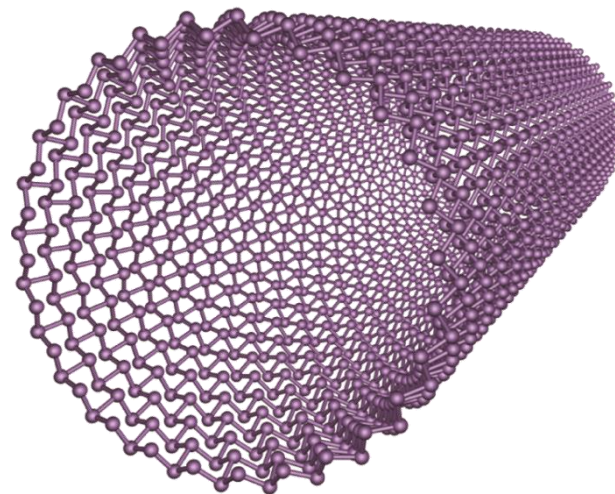

Figures: AJK

Literature



Structure and Bonding 139
Series Editor: D.M.P. Mingos

Thomas F. Fässler *Editor*

Zintl Phases

Principles and Recent Developments

 Springer

Structure and Bonding 140
Series Editor: D.M.P. Mingos

Thomas F. Fässler *Editor*

Zintl Ions

Principles and Recent Developments

 Springer

Main group elements

V·T·E

Periodic table of electronegativity by Pauling scale

→ Atomic radius decreases → Ionization energy increases → Electronegativity increases →

Group →	1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	18
↓ Period																		
1	H 2.20																	He
2	Li 0.98	Be 1.57											B 2.04	C 2.55	N 3.04	O 3.44	F 3.98	Ne
3	Na 0.93	Mg 1.31											Al 1.61	Si 1.90	P 2.19	S 2.58	Cl 3.16	Ar
4	K 0.82	Ca 1.00	Sc 1.36	Ti 1.54	V 1.63	Cr 1.66	Mn 1.55	Fe 1.83	Co 1.88	Ni 1.91	Cu 1.90	Zn 1.65	Ga 1.81	Ge 2.01	As 2.18	Se 2.55	Br 2.96	Kr 3.00
5	Rb 0.82	Sr 0.95	Y 1.22	Zr 1.33	Nb 1.6	Mo 2.16	Tc 1.9	Ru 2.2	Rh 2.28	Pd 2.20	Ag 1.93	Cd 1.69	In 1.78	Sn 1.96	Sb 2.05	Te 2.1	I 2.66	Xe 2.60
6	Cs 0.79	Ba 0.89	*	Hf 1.3	Ta 1.5	W 2.36	Re 1.9	Os 2.2	Ir 2.20	Pt 2.28	Au 2.54	Hg 2.00	Tl 1.62	Pb 1.87	Bi 2.02	Po 2.0	At 2.2	Rn 2.2
7	Fr 0.7	Ra 0.9	**	Rf	Db	Sg	Bh	Hs	Mt	Ds	Rg	Cn	Uut	Fl	Uup	Lv	Uus	Uuo
			*	La 1.1	Ce 1.12	Pr 1.13	Nd 1.14	Pm 1.13	Sm 1.17	Eu 1.2	Gd 1.2	Tb 1.1	Dy 1.22	Ho 1.23	Er 1.24	Tm 1.25	Yb 1.1	Lu 1.27
			**	Ac 1.1	Th 1.3	Pa 1.5	U 1.38	Np 1.36	Pu 1.28	Am 1.13	Cm 1.28	Bk 1.3	Cf 1.3	Es 1.3	Fm 1.3	Md 1.3	No 1.3	Lr 1.3

Metal/metalloid line

Figure: Wikipedia

Overview of main group compounds (1)

- Group 1+2 compounds
 - Not so relevant, but some interesting examples such as Laves phase CaLi_2
- Groups 1 + 17 and groups 2 + 17 (NaCl , MgCl_2 , ...)
- Typically simple salts (discussed previously)
- Halides known practically for all main groups 13-15
 - Mostly **molecular** for B, C, Si, Ge, Sn, group 15, and group 16 (e.g. SiCl_4 , PCl_5 , SF_6)
 - Mostly **non-molecular** for Al, Ga, In, Tl, Pb
 - Almost follows metal/metalloid line
- Oxides
 - Simple salts for groups 1 and 2 (e.g. MgO)
 - Stable oxides for groups 13-16, not for 17
 - Vast number of minerals
- Other chalcogenides (S, Se, Te)
 - Similarly to O, chalcogenides known practically for all main group elements (groups 1, 2, 13-15)

Figure: Wikipedia/AJK

1	2	13	14	15	16	17
H 2.20						
Li 0.98	Be 1.57	B 2.04	C 2.55	N 3.04	O 3.44	F 3.98
Na 0.93	Mg 1.31	Al 1.61	Si 1.90	P 2.19	S 2.58	Cl 3.16
K 0.82	Ca 1.00	Ga 1.81	Ge 2.01	As 2.18	Se 2.55	Br 2.96
Rb 0.82	Sr 0.95	In 1.78	Sn 1.96	Sb 2.05	Te 2.1	I 2.66
Cs 0.79	Ba 0.89	Tl 1.62	Pb 1.87	Bi 2.02	Po 2.0	At 2.2
Fr 0.7	Ra 0.9	Uut	Fl	Uup	Lv	Uus

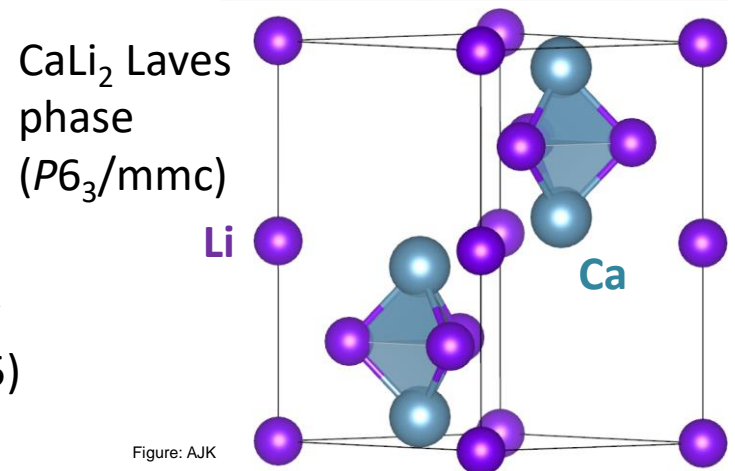


Figure: AJK

Overview of main group compounds (2)

- Group 1/2 + 14: Carbides, silicides, germanides, ...
 - CaC_2 , Mg_2Si , CaGe_2 , ...
- Group 1/2 + 15: Nitrides, phosphides, arsenides, ...
 - Li_3N , Li_3P , Li_3As , ...
- Main group compound semiconductors
 - 13-15 (BN, GaN, GaAs, etc.)
 - 14-16 (PbTe, PbSnTe, SnS, etc.)
 - 15-16 (Sb_2Se_3 , Bi_2Te_3 , etc.)
- Some elements are technologically extremely important as such or as simple alloys/compounds
 - Si, Ge, $\text{Si}_x\text{Ge}_{1-x}$, SiC (semiconductors)
 - Al and Mg as structural metals

Periodic table of electronegativity by Pauling scale

1	2	13	14	15	16	17
H 2.20						
Li 0.98	Be 1.57	B 2.04	C 2.55	N 3.04	O 3.44	F 3.98
Na 0.93	Mg 1.31	Al 1.61	Si 1.90	P 2.19	S 2.58	Cl 3.16
K 0.82	Ca 1.00	Ga 1.81	Ge 2.01	As 2.18	Se 2.55	Br 2.96
Rb 0.82	Sr 0.95	In 1.78	Sn 1.96	Sb 2.05	Te 2.1	I 2.66
Cs 0.79	Ba 0.89	Tl 1.62	Pb 1.87	Bi 2.02	Po 2.0	At 2.2
Fr 0.7	Ra 0.9	Uut	Fl	Uup	Lv	Uus

Figure: Wikipedia/AJK

Focus of the lecture:

Allotropes and Zintl phases

- Several main group elements show very rich **allotropy** in ambient pressure
 - Different structural modifications of the same element ([IUPAC Gold Book](#))
 - Highly interesting from fundamental scientific point of view, but also of high technological relevance (for example, allotropes of carbon)
 - Here we consider **atmospheric pressure** only!
- **Zintl phases** are an important class of main group compounds with connections to G14-16 allotropes
 - Include semiconductors with applications in thermoelectrics, etc.
- Key concept for the lecture: **isoelectronic principle**
 - Same number of **valence electrons** and the same structure (= number and connectivity of atoms), but different composition (CO vs. N₂)

13	14	15	16
B	C	N	O
Al	Si	P	S
Ga	Ge	As	Se
In	Sn	Sb	Te
Tl	Pb	Bi	Po

Main groups 13-16, elements showing allotropy highlighted

Allotropy

- Knowledgedoor.com has a good listing of allotropes with original references
 - http://www.knowledgedoor.com/2/elements_handbook/allotropes.html
- Note that many are for high pressure
- "Textbook"-level information, the most recent research not included
- <http://www.knowledgedoor.com/> is actually a rather good source of physical data (references to original data available)
- Let's focus on few examples of group 14, 15, and 16 allotropes

Allotropes Navigation


By Name ▼ | By Symbol ▼ | By Number ▼

1																	18
H	2														He		
Li	Be											B	C	N	O	F	Ne
Na	Mg	3	4	5	6	7	8	9	10	11	12	Al	Si	P	S	Cl	Ar
K	Ca	Sc	Ti	V	Cr	Mn	Fe	Co	Ni	Cu	Zn	Ga	Ge	As	Se	Br	Kr
Rb	Sr	Y	Zr	Nb	Mo	Tc	Ru	Rh	Pd	Ag	Cd	In	Sn	Sb	Te	I	Xe
Cs	Ba	Lu	Hf	Ta	W	Re	Os	Ir	Pt	Au	Hg	Tl	Pb	Bi	Po	At	Rn
Fr	Ra	Lr	Rf	Db	Sg	Bh	Hs	Mt	Ds	Rg	Cn	Uut	Fl	Uup	Lv	Uus	Uuo
		La	Ce	Pr	Nd	Pm	Sm	Eu	Gd	Tb	Dy	Ho	Er	Tm	Yb		
		Ac	Th	Pa	U	Np	Pu	Am	Cm	Bk	Cf	Es	Fm	Md	No		

Carbon

allotrope category	diamond	▼
allotrope	cubic diamond	▼
allotrope	hexagonal diamond	▼
alternate name	lonsdaleite	▼
allotrope category	graphite	▼
allotrope	hexagonal graphite	▼
alternate name	α-graphite	▼
allotrope	rhombohedral graphite	▼
alternate name	β-graphite	▼
allotrope	turbostratic graphite	▼
allotrope	chaoite	▼
allotrope category	fullerenes	▼
allotrope	fullerene-C ₆₀	▼
symbol	C ₆₀	▼
allotrope	fullerene-C ₇₀	▼
symbol	C ₇₀	▼

The allotropy of carbon

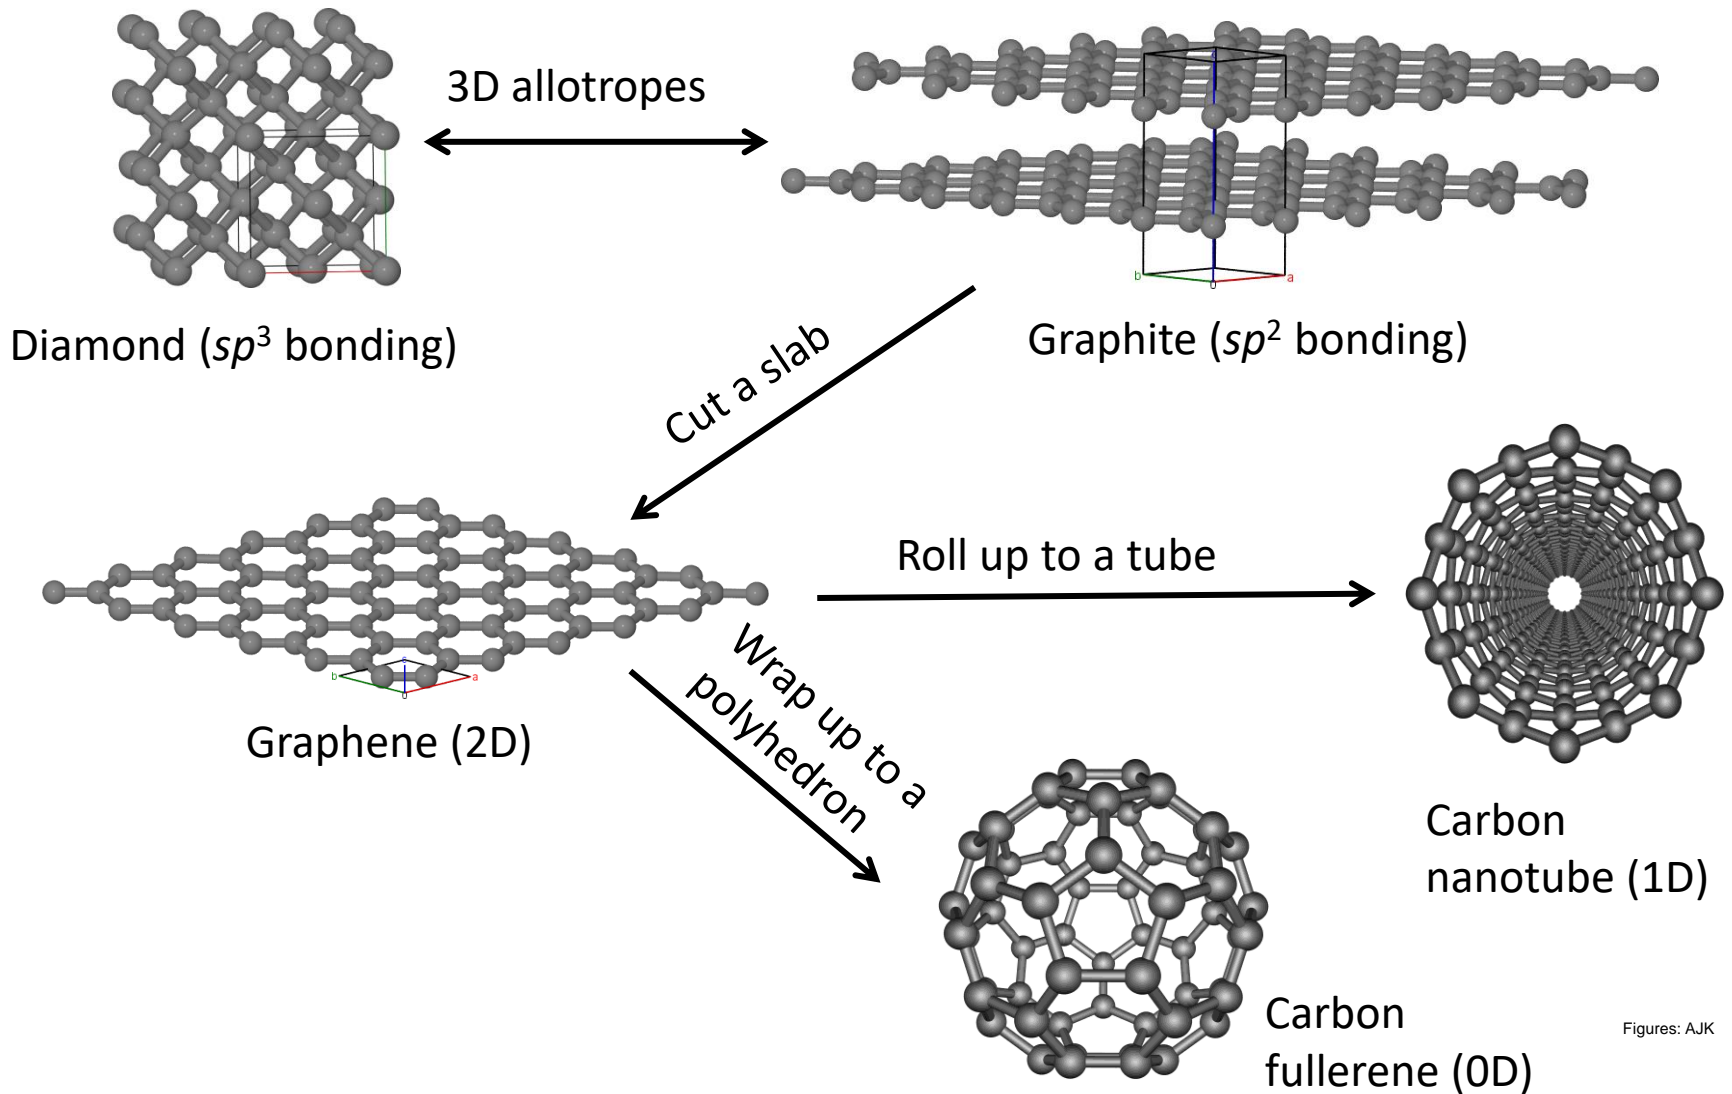

The allotropy of silicon

- Short overview available in: A. J. Karttunen, D. Usvyat, M. Schütz, L. Maschio, Dispersion interactions in silicon allotropes, *Phys. Chem. Chem. Phys.* **2017**, *19*, 7699 (DOI: [10.1039/c6cp08873b](https://doi.org/10.1039/c6cp08873b))

Table 1 Silicon allotropes included in this study. The structures are ordered according to their relative energy ΔE at the LMP2/TZVPP level (see below) from the most to the least stable structure

Pearson ^a	Name(s) ^b	Space group	a^c (Å)	b^c (Å)	c^c (Å)	k -Grid ^d	Notes
<i>cF8</i>	Alpha (α)/3C	<i>Fd$\bar{3}m$</i>	5.43			$12 \times 12 \times 12$	Diamond structure. Most stable Si allotrope under STP conditions.
<i>hP8</i>	4H	<i>P6$_3$/mmc</i>	3.83		12.59	$12 \times 12 \times 4$	Hexagonal polytype of 3C. 4H-Ge has been synthesized as a bulk material starting from <i>m-allo</i> -Ge. ^{62,63}
<i>hP4</i>	2H	<i>P6$_3$/mmc</i>	3.83		6.32	$12 \times 12 \times 6$	Hexagonal polytype of 3C. 2H-Si has been fabricated on GaP nanowire templates. ⁶⁴
<i>tP12</i>	cdp/T12	<i>PA$_2$/ncm</i>	5.19		9.24	$8 \times 8 \times 4$	Hypothetical allotrope, topology the same as in CdP $_2$. ^{16,65}
<i>oP32</i>	GAa4	<i>Pbcm</i>	7.85	11.29	7.45	$4 \times 4 \times 4$	The most stable building block of stacking-faulted <i>m-allo</i> -Ge (synthesized as a bulk material structure starting from Li $_7$ Ge $_{12}$). ^{17,63}
<i>hP6</i>	unj/NGS	<i>P6$_1$22</i>	5.44		5.08	$8 \times 8 \times 8$	Hypothetical allotrope, topology the same as for the Ga-Sn network in NaGaSn $_5$. ^{17,66}
<i>tP24</i>	tum1	<i>PA$_2$/nmc</i>	7.42		9.15	$6 \times 6 \times 4$	Hypothetical allotrope, topology the same as for the B-Si network in LiBSi $_2$. ⁶⁷
<i>oC24</i>	CAS	<i>Cmcm</i>	3.82	10.68	12.66	$8 \times 8 \times 4$	Has been synthesized from Na $_4$ Si $_{24}$. ⁶⁸
<i>cF136</i>	Clathrate II	<i>Fd$\bar{3}m$</i>	14.65			$4 \times 4 \times 4$	Has been synthesized from Na $_x$ Si $_{136}$, ^{4,5} also known for Ge. ⁷
<i>cI46</i>	Clathrate VIII	<i>I$\bar{4}3m$</i>	10.04			$4 \times 4 \times 4$	Hypothetical allotrope, experimentally known in type-VIII Ge and Sn clathrates. ^{13,69,70}
<i>cP46</i>	Clathrate I	<i>Pm$\bar{3}n$</i>	10.16			$4 \times 4 \times 4$	Hypothetical allotrope, experimentally known in Na $_8$ Si $_{46}$ type-I clathrate. ^{13,69,70}

Open-framework allotrope of Si

nature
materials


LETTERS

PUBLISHED ONLINE: 17 NOVEMBER 2014 | DOI: 10.1038/NMAT4140

Synthesis of an open-framework allotrope of silicon

Duck Young Kim^{1†}, Stevce Stefanoski^{1†}, Oleksandr O. Kurakevych^{1,2‡} and Timothy A. Strobel^{1*†}

Silicon is ubiquitous in contemporary technology. The most stable form of silicon at ambient conditions takes on the structure of diamond (cF8, *d*-Si) and is an indirect bandgap semiconductor, which prevents it from being considered as a next-generation platform for semiconductor technologies^{1–4}. Here, we report the formation of a new orthorhombic allotrope of silicon, Si₂₄, using a novel two-step synthesis methodology. First, a Na₄Si₂₄ precursor was synthesized at high pressure⁵; second, sodium was removed from the precursor by a thermal 'degassing' process. The *Cmcm* structure of Si₂₄, which has 24 Si atoms per unit cell (oC24), contains open channels along the crystallographic *a*-axis that are formed from six- and eight-membered *sp*³ silicon rings. This new allotrope possesses a quasidirect bandgap near 1.3 eV. Our combined experimental/theoretical study expands the known allotropy for element fourteen and the unique high-pressure precursor synthesis methodology demonstrates the potential for new materials with desirable properties.

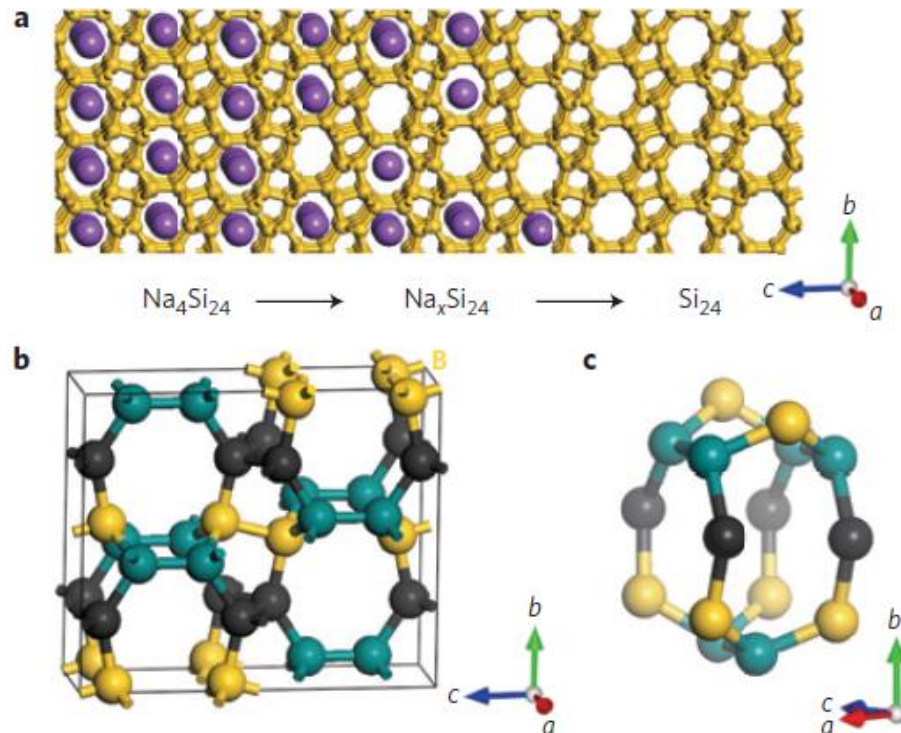

Si₁₃₆ and Ge₁₃₆ allotropes

On the clathrate form of elemental silicon, Si₁₃₆:
preparation and characterisation of Na_xSi₁₃₆ ($x \rightarrow 0$)

Abdelaziz Ammar^{a,1}, Christian Cros^{a,*}, Michel Pouchard^a, Nicolas Jaussaud^a,
Jean-Marc Bassat^a, Gérard Villeneuve^b, Mathieu Duttine^b, Michel Ménétrier^a, Edouard Reny^a
Solid State Sciences 6 (2004) 393–400

Vacuum route

NATURE | Vol 443 | 21 September 2006

LETTERS

A guest-free germanium clathrate

Ionic liquid route,
discussed in a later slide


Arnold M. Guloy^{1,2}, Reiner Ramlau¹, Zhongjia Tang^{1,2}, Walter Schnelle¹, Michael Baitinger¹ & Yuri Grin¹

Clathrate-II
(*Fd-3m*)

Known for:

Si₁₃₆


Ge₁₃₆

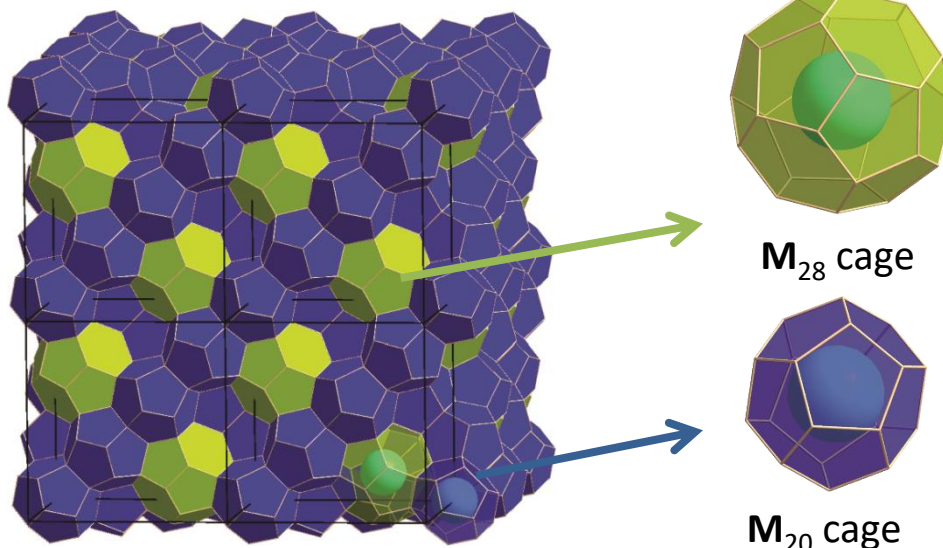

(**M** = Si, Ge)
Normally the cages
are occupied by
guest atoms (Na, K,
etc.), but the guests
can be removed


Ge and Sn allotropes

J. Mater. Chem. **2010**, *20*, 1780–1786 ([DOI](#))

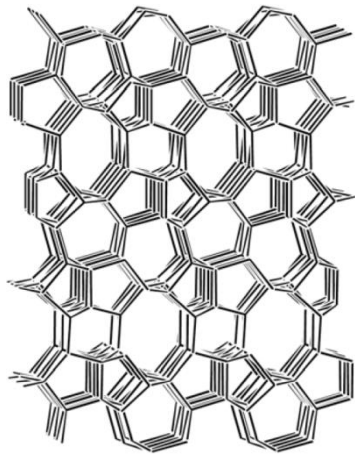


m-allo-Ge

140°C

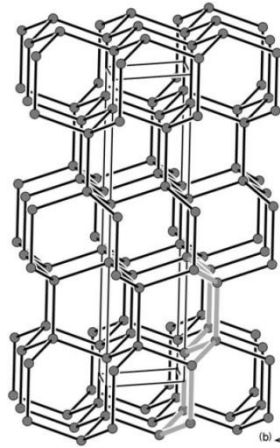



4H-Ge ($P6_3/mmc$)

400°C

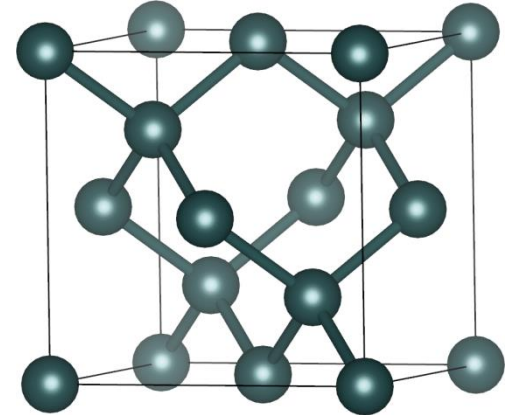


α -Ge ($Fd-3m$)

β -Sn ($I4_1/amd$)
white tin

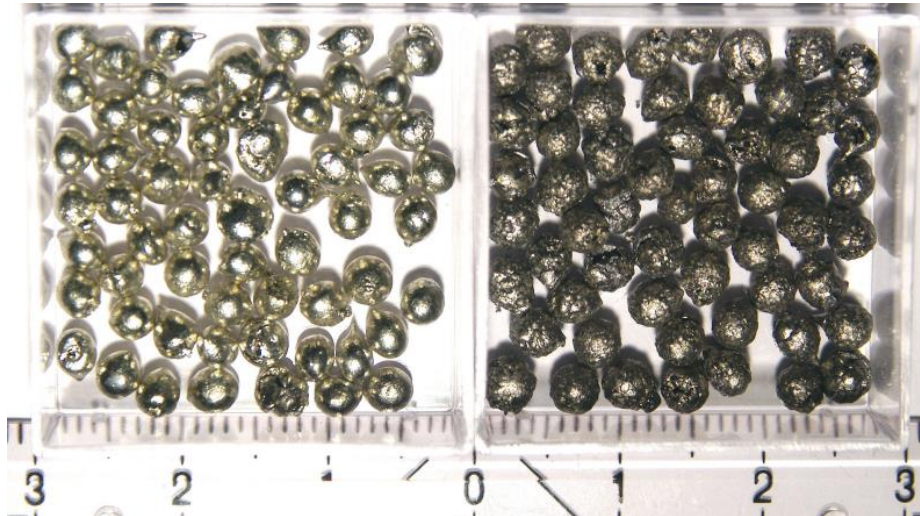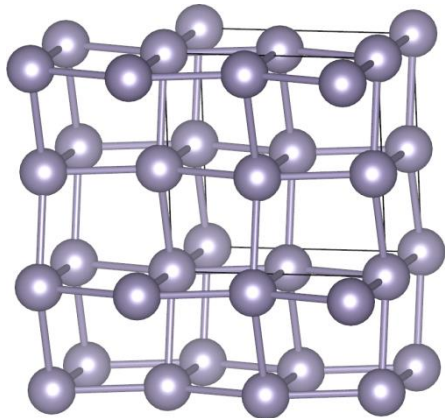


α -Sn ($Fd-3m$)
grey tin

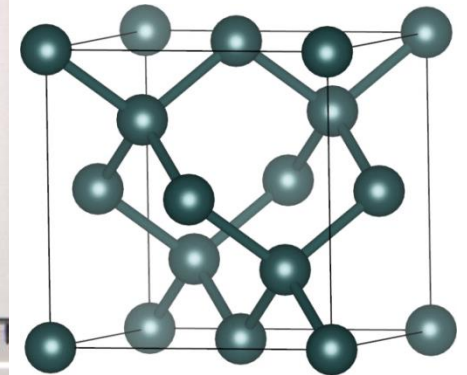


<https://crystallography365.wordpress.com/2014/11/23/a-failed-campaign-alpha-and-beta-tin/>
https://en.wikipedia.org/wiki/Tin_pest#Napoleon.27s_buttons

Group 15 allotropic modifications

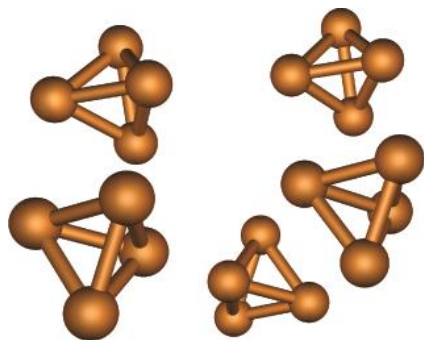


Tetrahedral molecules
(P_4 , As_4 , Sb_4)
White phosphorus

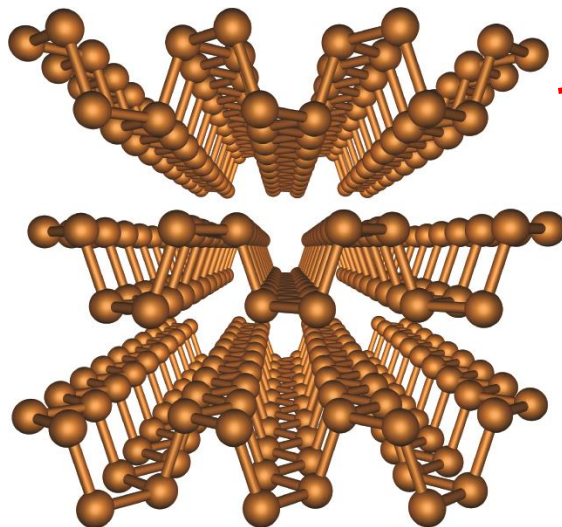


Orthorhombic layered
structure, $Cmca$ (P, As)
Black phosphorus




Individual sheets can be cleaved
-> phosphorene

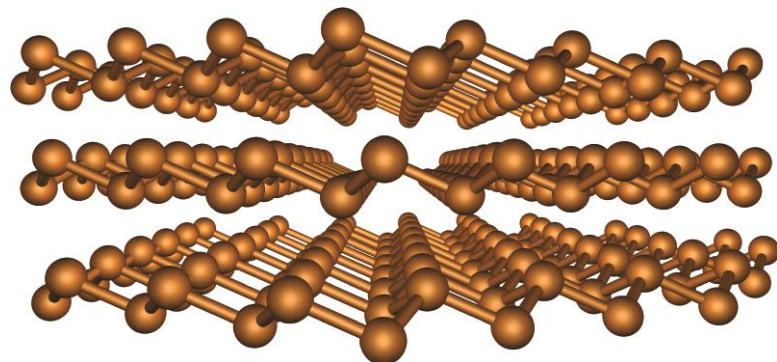

Trigonal layered structure, $R-3m$ (P in
high pressure, As, Sb, Bi)

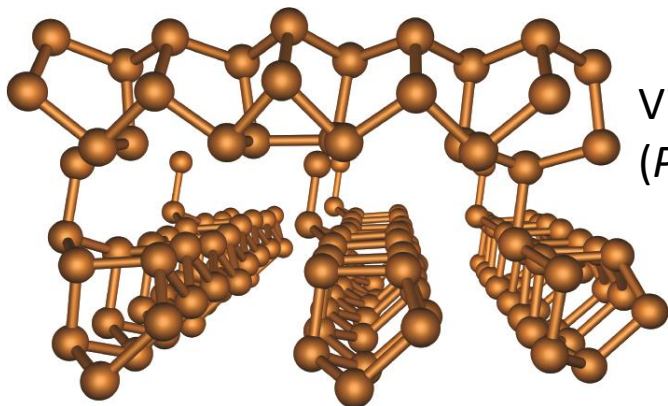

Violet phosphorus
($P2/c$)

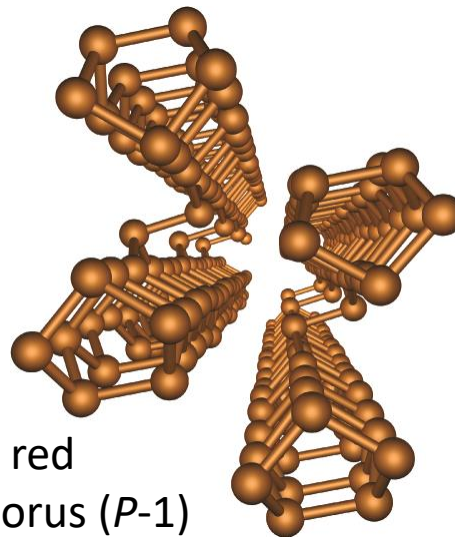


Fibrous red
phosphorus ($P-1$)

Group 15 nanostructures

Analogous to the carbon fullerenes and nanotubes, but possess puckered atomic structure


Polyhedra (e.g. P₁₈₀)

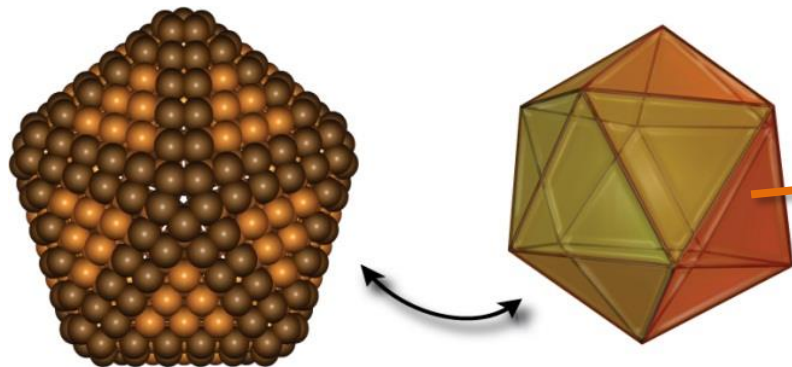

Chem. Eur. J. **2007**, *13*, 5232 ([DOI](#))


Theor. Chem. Acc. **2011**, *129*, 412 ([DOI](#))

Bismuth nanoicosahedra

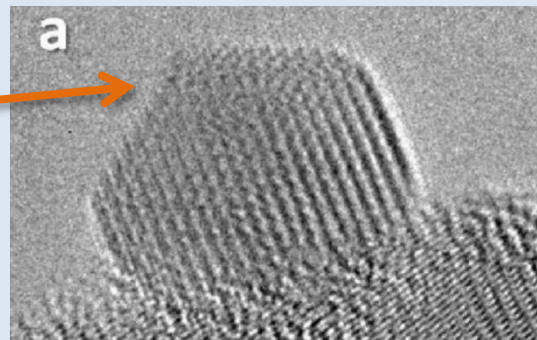


Y. Selzer et al, *Nano Lett.* **2012**, *12*, 1087.

Nanotubes

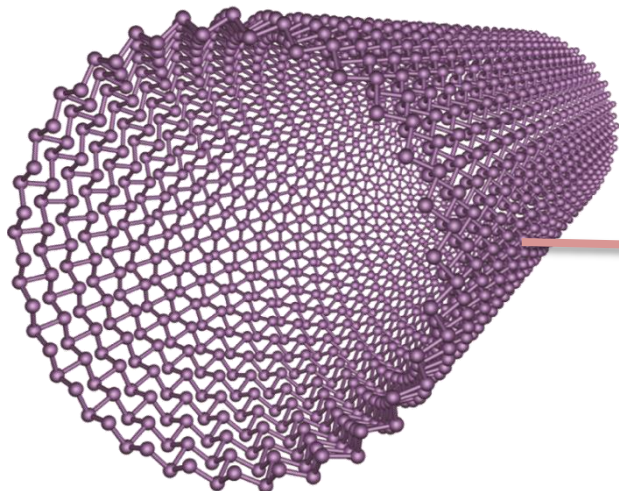


Bismuth nanotubes

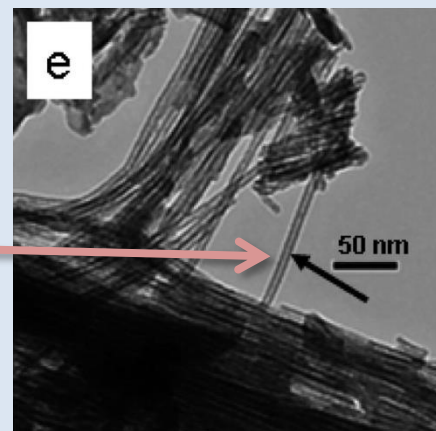


Pfefferle et al, *J. Phys. Chem. C*, **2010**, *114*, 3431.

Phosphorus nanostructures


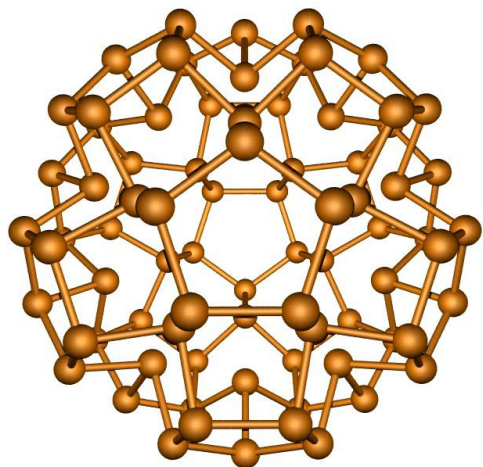


P_{80} fullerene (I_h)

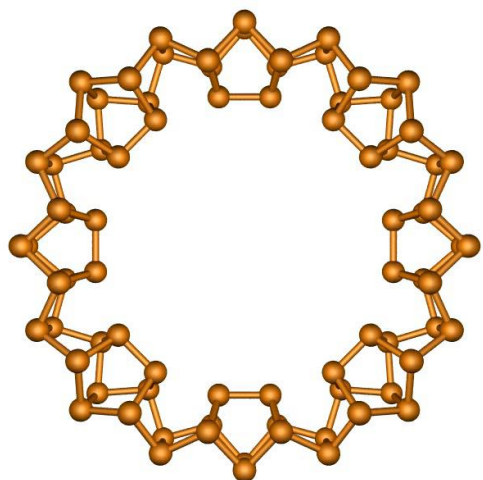


P_{80} ring (C_{4v})


Icosahedral and Ring-shaped Allotropes of Phosphorus
Karttunen, A. J.; Linnolahti, M.; Pakkanen, T. A.
Chem. Eur. J. **2007**, *13*, 5232–5237 ([DOI](#)).

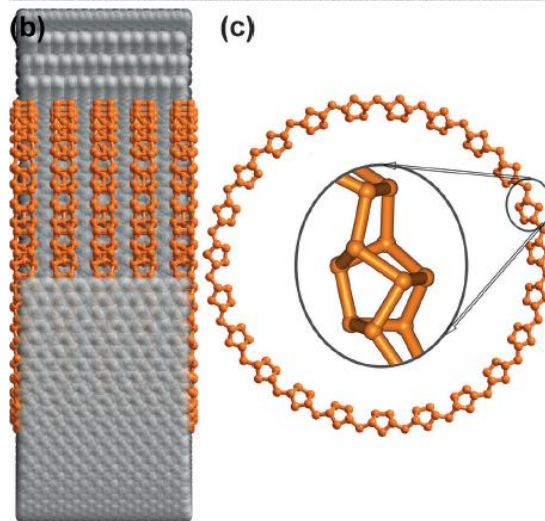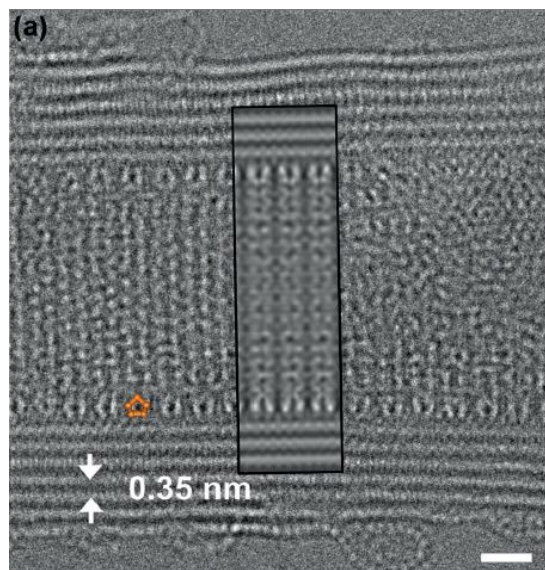

Assembly of Ring-Shaped Phosphorus within Carbon
Nanotube Nanoreactors, Zhang *et al.*
Angew. Chem. Int. Ed. **2017**, *56*, 1850-1854 ([DOI](#)).

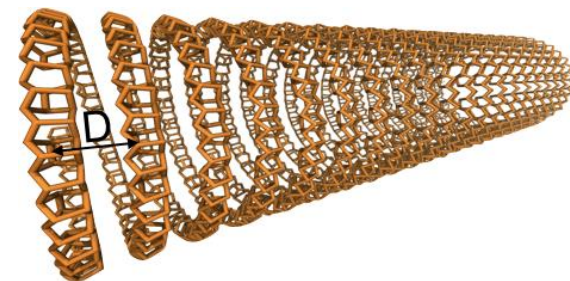


Red phosphorus helices

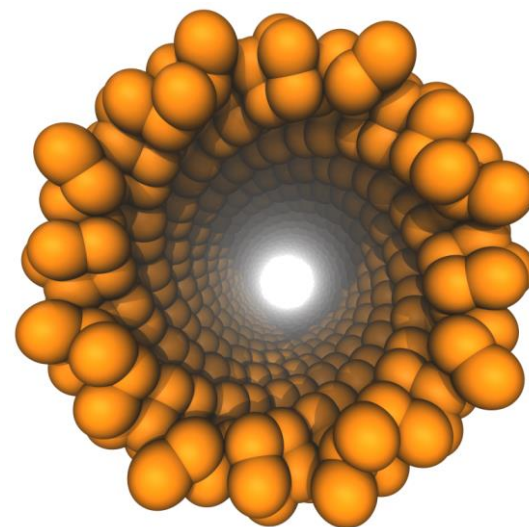


One-dimensional Phosphorus Nanostructures: from
Nanorings to Nanohelices
Sansone, G.; Maschio, L.; Karttunen, A. J. *Chem. Eur. J.*
2017, *23*, 15884–15888. ([DOI](#)).

Group 16 allotropes


- Whereas the allotropes of group 15 elements are three-coordinate, the additional valence electron of group 16 elements makes their allotropes two-coordinate
- This imposes limits on the capability to form infinite structural networks, but the elemental chemistry of S and Se is still very rich
- The only known crystalline form of Te at room pressure is similar to gray Se

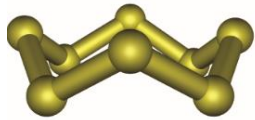

α -cyclo-S₈ (*Fddd*)

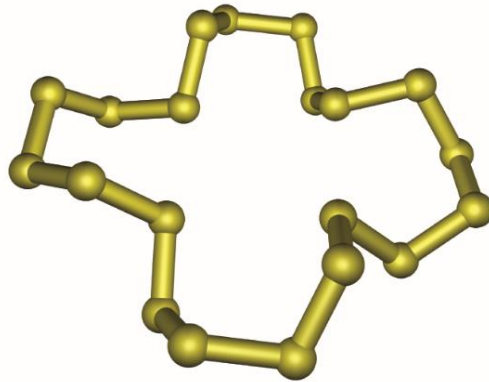

Cyclo-S₂₀ (*Pbcn*)

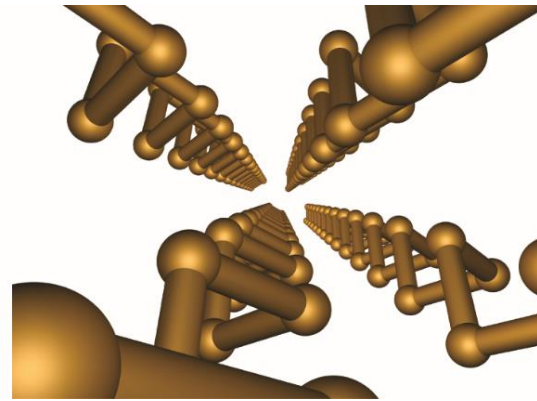

Gray selenium consisting of helical chains (*P3₁21*)

Zintl phases

- Zintl phases are **valence-balanced** semiconductors
 - Charge transfer from Group 1 or 2 elements to Group 13-16 elements
- For example, NaTl (sodium thallide)
 - Each Na atom donates $1e^-$
 - Each Tl atom accepts $1e^-$
- The electron configuration of the anionic Tl network is now **analogous to group 14 elements**
 - Tl atoms adopt 4-coordinated diamond structure
 - The Na^+ ions are packed as diamond, too
 - Covalent bonding within the Tl network, ionic bonding between the anionic network and the cations (or mixed ionic / covalent)
- Basically, **the 8-electron rule** in action
- Ideally, Zintl phases should be **semiconducting**
 - However, in reality many are metallic (e.g. NaTl)
 - Bonding is more complex than the ideal "valence-balanced" (or there are impurities)

Periodic table of electronegativity by Pauling scale

1	2	13	14	15	16	17
H 2.20						
Li 0.98	Be 1.57	B 2.04	C 2.55	N 3.04	O 3.44	F 3.98
Na 0.93	Mg 1.31	Al 1.61	Si 1.90	P 2.19	S 2.58	Cl 3.16
K 0.82	Ca 1.00	Ga 1.81	Ge 2.01	As 2.18	Se 2.55	Br 2.96
Rb 0.82	Sr 0.95	In 1.78	Sn 1.96	Sb 2.05	Te 2.1	I 2.66
Cs 0.79	Ba 0.89	Tl 1.62	Pb 1.87	Bi 2.02	Po 2.0	At 2.2
Fr 0.7	Ra 0.9	Uut 1.62	Fl 1.87	Uup 2.02	Lv 2.0	Uus 2.2

Figure: Wikipedia/AJK


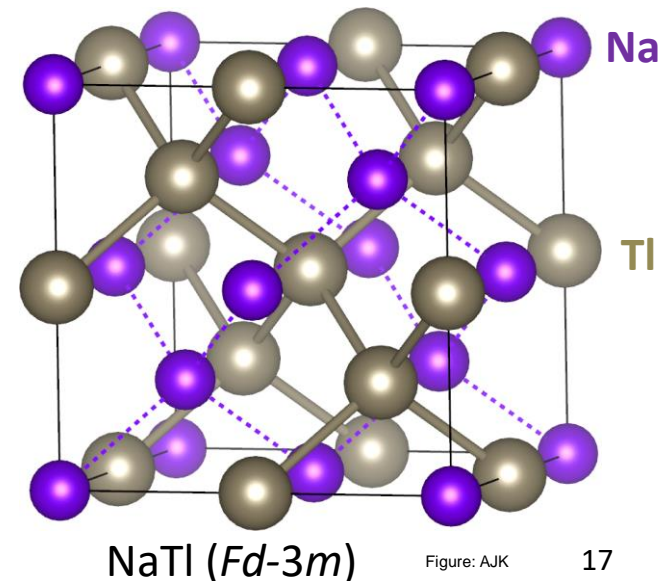


Figure: AJK

Examples of Zintl phases (1)


NaSi (Na_4Si_4)

- Each Na atom donates $1e^-$
- Each Si atom accepts $1e^-$
- Si_4^{4-} tetrahedra are isoelectronic with P_4 tetrahedra (white phosphorus)

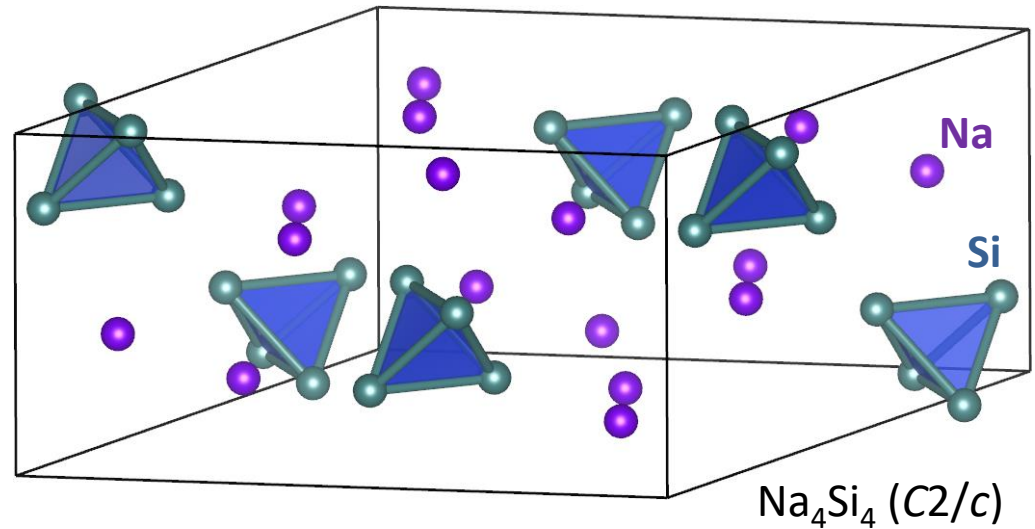

MgB₂


- Each Mg atom donates $2e^-$
- Each B atom accepts $1e^-$
- The resulting two-dimensional B-network is isoelectronic with graphene

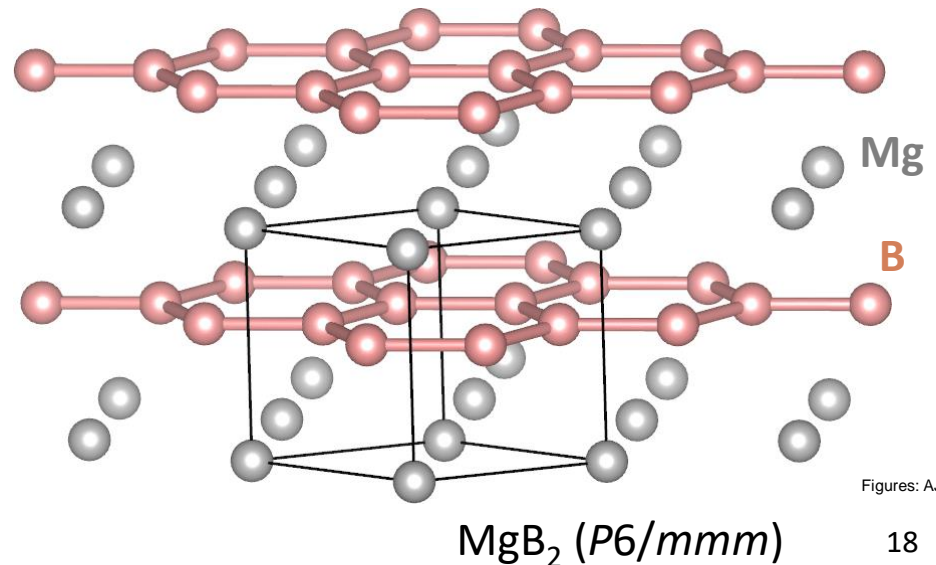

Examples of Zintl phases (2)


CaSi

- Each Ca atom donates $2e^-$
- Each Si atom accepts $2e^-$
- The resulting one-dimensional Si-chains are closely related to Se-chains (but planar, not helical)

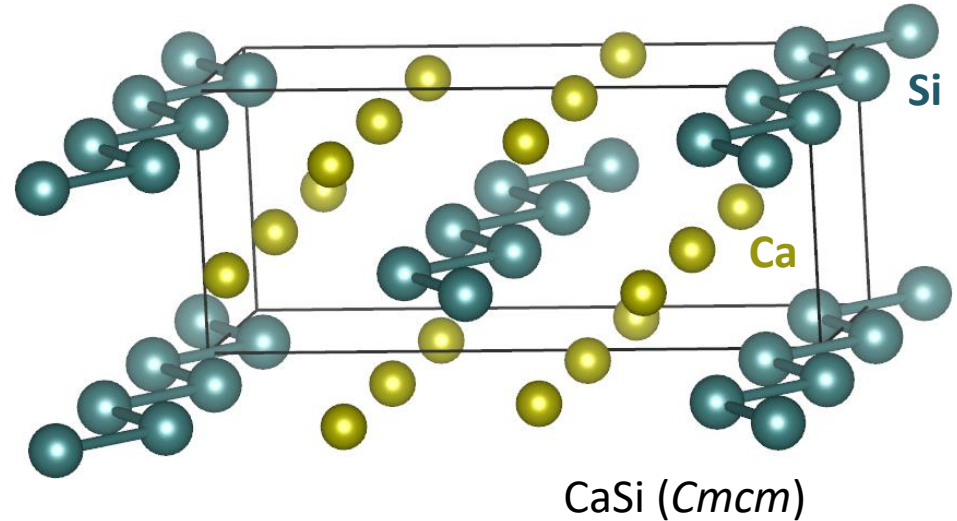

CaSi₂

- Each Ca atom donates $2e^-$
- Each Si atom accepts $1e^-$
- The resulting two-dimensional Si-network is isoelectronic and structurally analogous with As / Sb / Bi

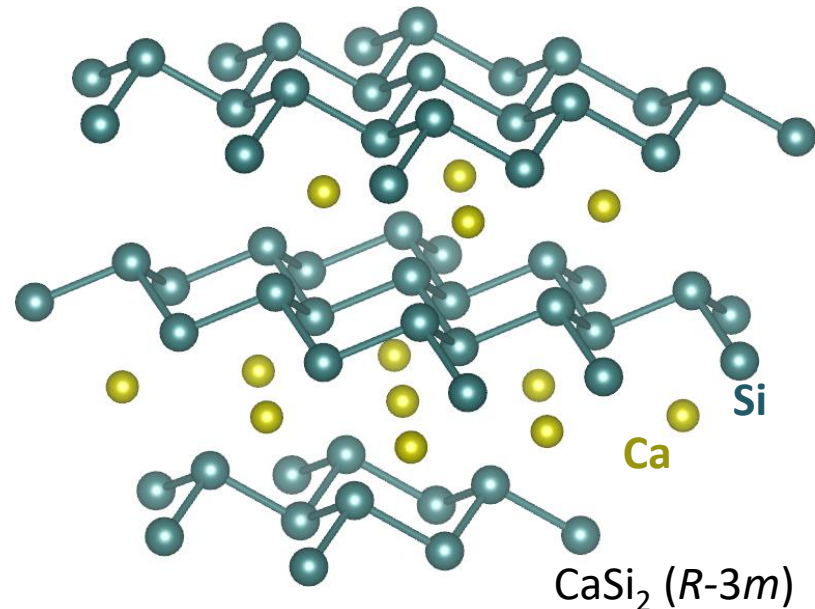


Group 14 Zintl ions (Si, Ge, Sn, Pb)

Many solid-state Zintl phases contain discrete anions

For example,
 $[\text{Ge}_9]^{4-}$ in Na_4Ge_9

Figure: Sandra Scharfe / [Dissertation](#) 2010 (TUM)

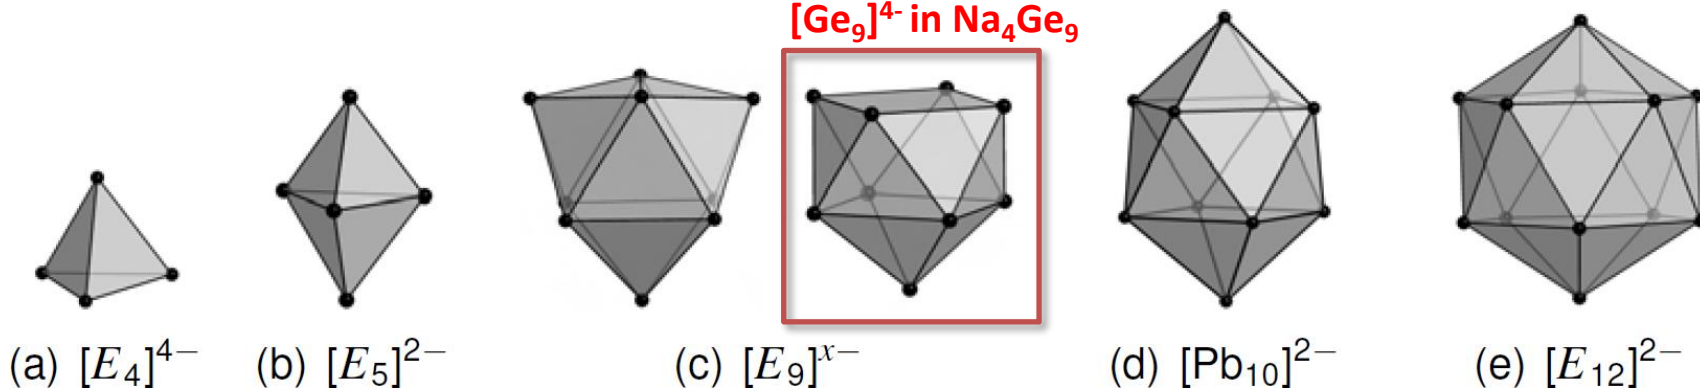

$[\text{Si}_4]^{4-}$ in
 Na_4Si_4

Strained bond angles in comparison to diamond-like bulk α -Si / α -Ge / α -Sn with 109.5° angles



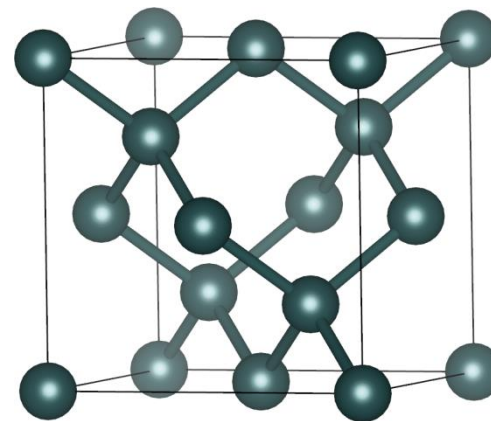


Figure: AJK

Zintl Ions, Cage Compounds, and Intermetalloid Clusters of Group 14 and Group 15 Elements, S. Scharfe, F. Kraus, S. Stegmaier, A. Schier, T. F. Fässler, *Angew. Chem. Int. Ed.* **2011**, *50*, 3630–3670 ([DOI](#)).

Zintl ions can be crystallized from solution

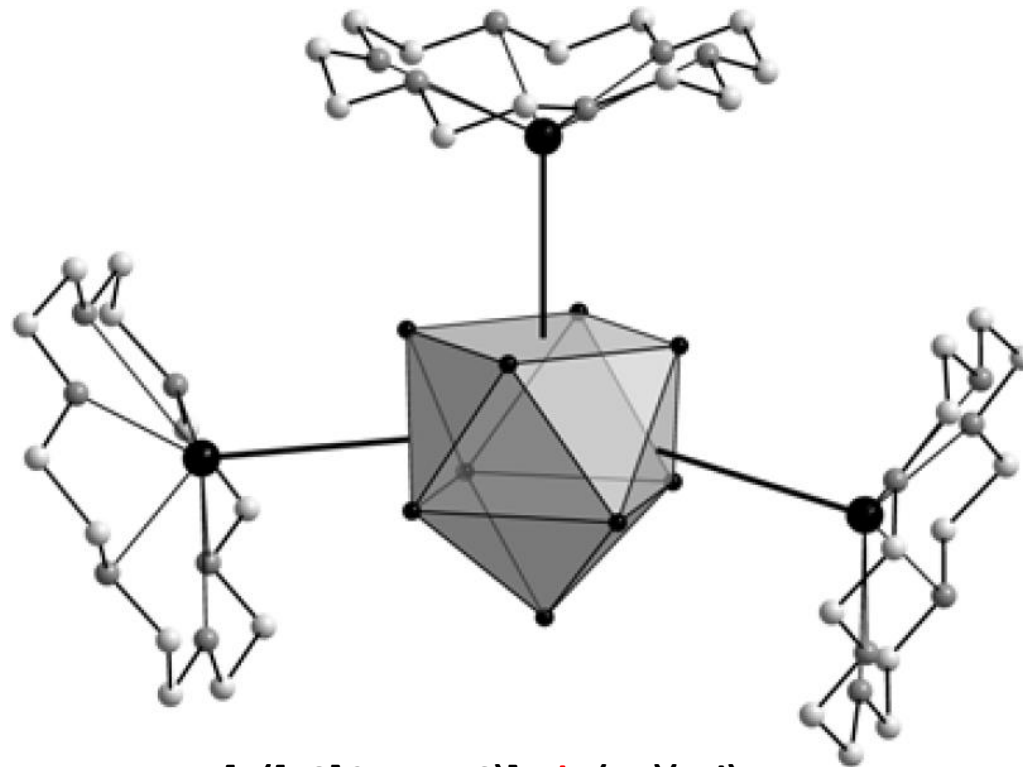

S. Scharfe, [Dissertation](#), Technical University of Munich, 2010


Zintl phases as precursors for preparing novel materials

NATURE|Vol 443|21 September 2006

LETTERS


A guest-free germanium clathrate

Arnold M. Guloy^{1,2}, Reiner Ramlau¹, Zhongjia Tang^{1,2}, Walter Schnelle¹, Michael Baitinger¹ & Yuri Grin¹

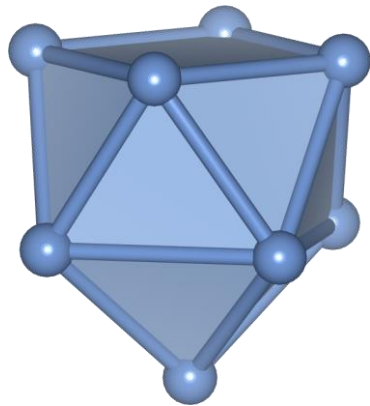

$[\text{Ge}_9]^{4-}$ (in Na_4Ge_9)

Mild oxidation in ionic liquid

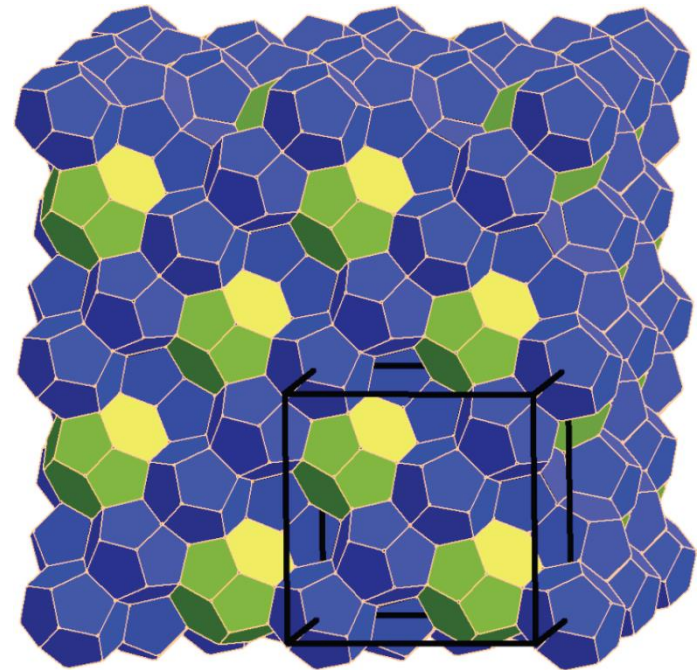


Ge_{136} Clathrate-II ($cF136$)

Zintl phases:

Semiconducting group 14 clathrates (1)

- The microporous 3D framework of the group 14 clathrates is composed of fused atomic cages
- The cages are normally occupied by guest atoms, but guest-free Si- and Ge-frameworks are known, as well
- The group 14 clathrates are excellent thermoelectric materials¹
 - Great thermal properties
 - Good electronic properties

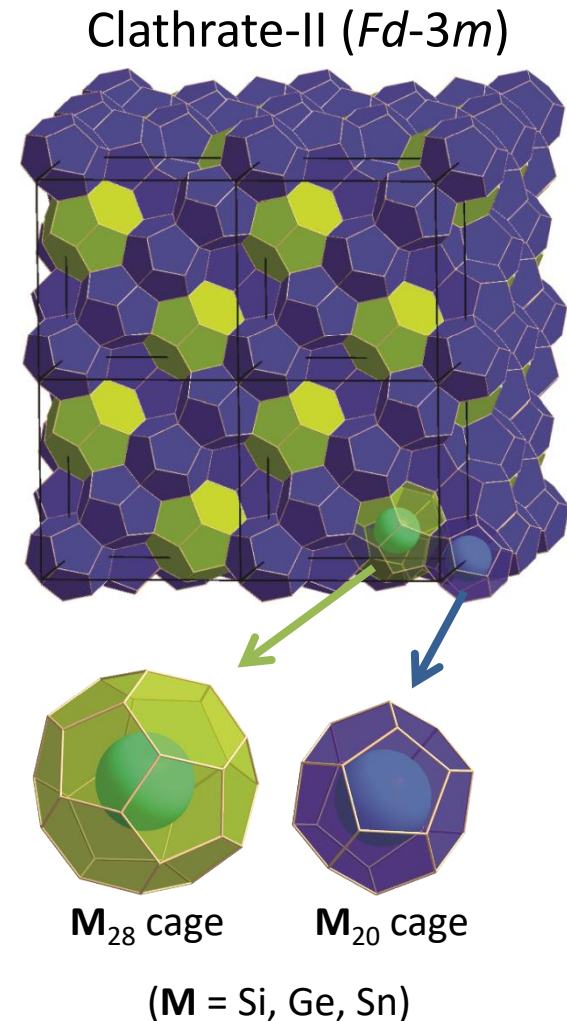


¹ G. S. Nolas et al. *Phys. Rev. Lett.*, **1999**, 82, 779.
G. S. Nolas et al. *J. Mater. Chem.*, **2008**, 18, 842.
B. B. Iversen et al. *Dalton Trans.*, **2010**, 39, 978.

Zintl phases:

Semiconducting group 14 clathrates (2)

- Charge transfer occurs between the guest and the framework
- The charge is (usually) balanced by heteroatoms in the framework
 - Metallic systems such as $\text{Na}_{24}\text{Si}_{136}$ are also known
- **The atomic composition and properties are somewhat tunable**

Clathrate-I ($Pm-3n$, 46 framework atoms in the unit cell)

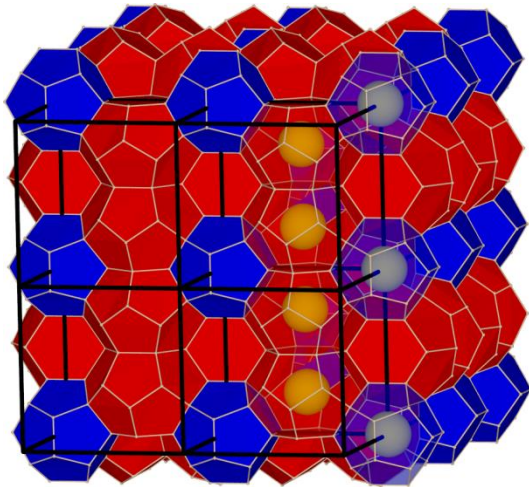

- $\text{Ba}_8[\text{Ga}_{16}\text{Ge}_{30}]$ (**anionic** framework)
- Each Ba atom donates $2e^-$
- Ga atoms have $1e^-$ less than Ge, so the 4-coordinated framework needs $16e^-$


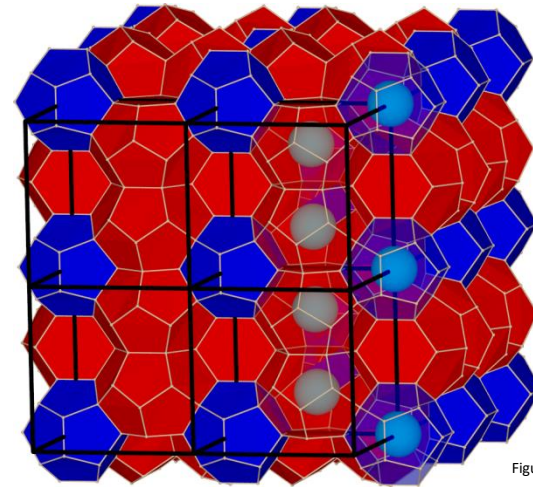


Figure: AJK


- $\text{I}_8[\text{As}_8\text{Ge}_{38}]$ (**cationic** framework!)
- Each I atom accepts $1e^-$
- As atoms have $1e^-$ more than Ge, these extra electrons are donated to the I atoms

Examples of clathrate frameworks


Very rich structural chemistry (all frameworks are not yet known for group 14 clathrates)

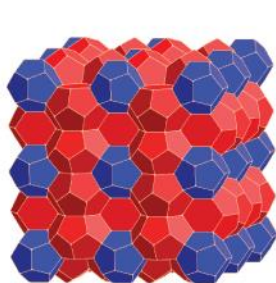


I ($Pm-3n$)

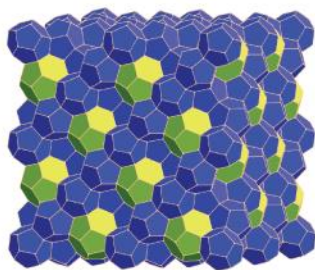


II ($Fd-3m$)

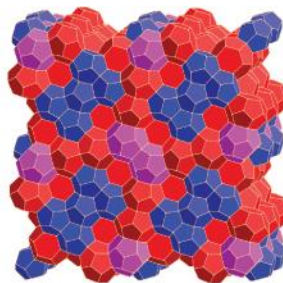

III ($P4_2/mnm$)

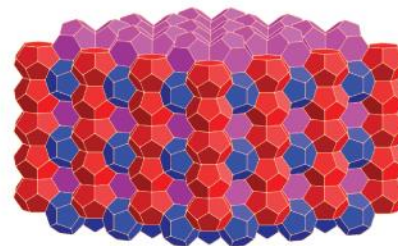


IV ($P6/mmm$)

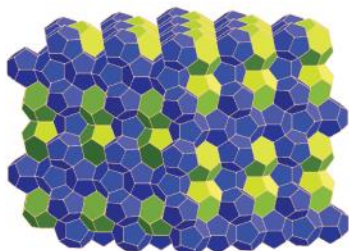


V ($P6_3/mmc$)



VI ($I-43d$)




VII ($Im-3m$)




VIII ($I-43m$)




H ($P6/mmm$)

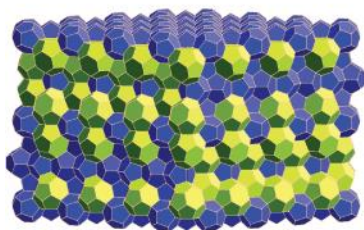


"II-4H" ($P6_3/mmc$)

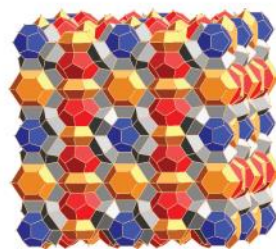

I-100 ($Pm-3n$)

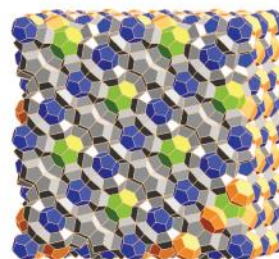

II-100 ($Fd-3m$)

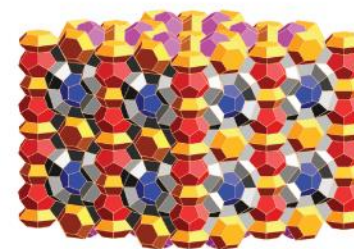

IV-100 ($P6/mmm$)

Currently known group 14 clathrates

		1											18																					
		H											He																					
		2											13	14	15	16	17																	
		Li	Be											B	C	N	O	F	Ne															
Guest atoms			Na	Mg	3	4	5	6	7	8	9	10	11	12	Al	Si	P	S	Cl	Ar														
			K	Ca	Sc	Ti	V	Cr	Mn	Fe	Co	Ni	Cu	Zn	Ga	Ge	As	Se	Br	Kr														
			Rb	Sr	Y	Zr	Nb	Mo	Tc	Ru	Rh	Pd	Ag	Cd	In	Sn	Sb	Te	I	Xe														
			Cs	Ba	La	Hf	Ta	W	Re	Os	Ir	Pt	Au	Hg	Tl	Pb	Bi	Po	At	Rn														
			<table border="1"> <tr> <td>Ce</td><td>Pr</td><td>Nd</td><td>Pm</td><td>Sm</td><td>Eu</td><td>Gd</td><td>Tb</td><td>Dy</td><td>Ho</td><td>Er</td><td>Tm</td><td>Yb</td><td>Lu</td> </tr> </table>																		Ce	Pr	Nd	Pm	Sm	Eu	Gd	Tb	Dy	Ho	Er	Tm	Yb	Lu
	Ce	Pr	Nd	Pm	Sm	Eu	Gd	Tb	Dy	Ho	Er	Tm	Yb	Lu																				

200+ phases are currently known. Typical synthesis routes:

- Shake & Bake
- Flux method
- Czochralski pulling

Shevelkov, A. V.; Kovnir, K. *Struct. Bond.* **2011**, 139, 97.

Recent review: Dolyniuk, J.-A.; Owens-Baird, B.; Wang, J.; Zaikina, J. V.; Kovnir K. *Materials Science and Engineering*, **2016**, R108, 1–46

Examples of clathrate phases

Si-based	Ge-based	Ge-based	Sn-based
$\text{Na}_8[\text{Si}_{46}]$	$\text{K}_8[\text{Al}_8\text{Ge}_{38}]$	$\text{I}_8[\text{Ge}_{38}\text{P}_8]$	$\text{K}_{1.6}\text{Cs}_{6.4}[\text{Sn}_{44}\square_2]$
$\text{Na}_{8-x}\text{Ba}_x[\text{Si}_{46}]$	$\text{Rb}_8[\text{Al}_8\text{Ge}_{38}]$	$\text{Br}_8[\text{Ge}_{38}\text{P}_8]$	$\text{Rb}_8[\text{Sn}_{44.6}\square_{1.4}]$
$\text{Na}_x\text{Ba}_6[\text{Si}_{46}]$	$\text{K}_8[\text{Ga}_8\text{Ge}_{38}]$	$\text{Cl}_8[\text{Ge}_{38}\text{P}_8]$	$\text{Cs}_8[\text{Sn}_{44}\square_2]$
$\text{K}_{7.62}\square_{0.38}[\text{Si}_{46}]$	$\text{Rb}_8[\text{Ga}_8\text{Ge}_{38}]$	$\text{I}_8[\text{Ge}_{38}\text{As}_8]$	$\text{K}_8[\text{Al}_8\text{Sn}_{38}]$
$\text{Rb}_{6.15}\square_{1.85}[\text{Si}_{46}]$	$\text{Cs}_8[\text{Ga}_8\text{Ge}_{38}]$	$\text{Br}_8[\text{Ge}_{38}\text{As}_8]$	$\text{Rb}_8[\text{Al}_8\text{Sn}_{38}]$
$\text{K}_8[\text{Ga}_8\text{Si}_{38}]$	$\text{K}_8[\text{In}_8\text{Ge}_{38}]$	$\text{Cl}_8[\text{Ge}_{38}\text{As}_8]$	$\text{K}_8[\text{Ga}_8\text{Sn}_{38}]$
$\text{Rb}_8[\text{Al}_8\text{Si}_{38}]$	$\text{Rb}_8[\text{In}_8\text{Ge}_{38}]$	$\text{I}_8[\text{Ge}_{38}\text{Sb}_8]$	$\text{Rb}_8[\text{Ga}_8\text{Sn}_{38}]$
$\text{Rb}_8[\text{Ga}_8\text{Si}_{38}]$	$\text{Cs}_8[\text{In}_8\text{Ge}_{38}]$	$\text{Br}_8[\text{Ge}_{38}\text{Sb}_8]$	$\text{Cs}_8[\text{Ga}_8\text{Sn}_{38}]$
		$\text{I}_8[\text{Ge}_{14}\text{Ga}_{12}\text{Sb}_{20}]$	$\text{Cs}_8[\text{Zn}_4\text{Sn}_{42}]$
			$\text{Cs}_8[\text{Cd}_4\text{Sn}_{42}]$