



Aalto University
School of Chemical
Technology

Nanocellulose: preparation and modification

CHEM-E2140

Cellulose-based fibres

Eero Kontturi

12th October 2021

Learning objectives

After this lecture, you should be able to:

- Explain why nanocellulose is important
- Distinguish cellulose nanofibres (CNFs) and cellulose nanocrystals (CNCs)
- List the main preparation routes to CNFs and CNCs
- List the main challenges in CNF and CNC preparation
- Be aware of the main approaches and bottlenecks in chemical modification of CNFs and CNCs

Outline

- (1) Different types of nanocellulose: Terminological issues
- (2) Preparation of nanocellulose:
 - Cellulose nanofibres (CNF) (including bacterial cellulose)
 - Cellulose nanocrystals (CNC)
- (3) Modification of CNF
- (4) Modification of CNC
- (5) Summary: comparison between CNF and CNC

Types of nanocellulose

(1) Cellulose nanofibres

- mechanically isolated microfibrils
- chemically isolated microfibrils (TEMPO-oxidation)
- bacterial cellulose

(2) Cellulose nanocrystals

- rods of highly crystalline cellulose, isolated by acid hydrolysis

Types of nanocellulose: terminological issues

(1) Cellulose nanofibres

Synonyms (used in literature) for mechanically isolated nanofibrillar cellulose:


- microfibrillar cellulose
- cellulose nanofibrils
- cellulose microfibrils

(2) Cellulose nanocrystals

Synonyms used in literature:

- cellulose whiskers
- cellulose nanowhiskers
- cellulose microfibrils
- **microcrystalline cellulose**
- nanocrystalline cellulose

Note: microcrystalline cellulose is in its more common use a completely different material (micron-sized cellulose crystals).

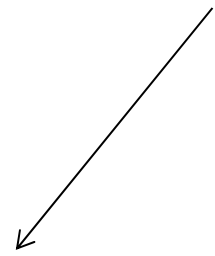

Why do we want nanocellulose?



Alternatives to non-renewable materials

- Reduce the use of, e.g., fossil-based components for materials
- Ultimate goal: renewable, biodegradable materials with unique properties

Why nanocellulose?

- High strength
- Low density
- Renewable and abundant
- Very high aspect ratio (length/width especially in the case of nanofibrils)
- Can be chemically modified for functional properties
- Specific response to water

Why do we want nanocellulose?



Example

Nanocomposite made of poly(lactic acid) as a continuous matrix and nanofibrillar cellulose as the reinforcing phase
→ Fully bio-based and biodegradable alternative to plastics

Other potential applications


- Viscosity modifiers
- Hydrogels for tissue growth
- Hydrogels for wound healing
- Drug release matrices
- Sensor materials
- Paper-based electronics
- Templates for chiral materials
- Platforms for asymmetric catalysis
- Security papers (liquid crystal phases)

Cellulose nanofibres: preparation

Ultrastructure of native cellulose


Individual fibre

10 μm

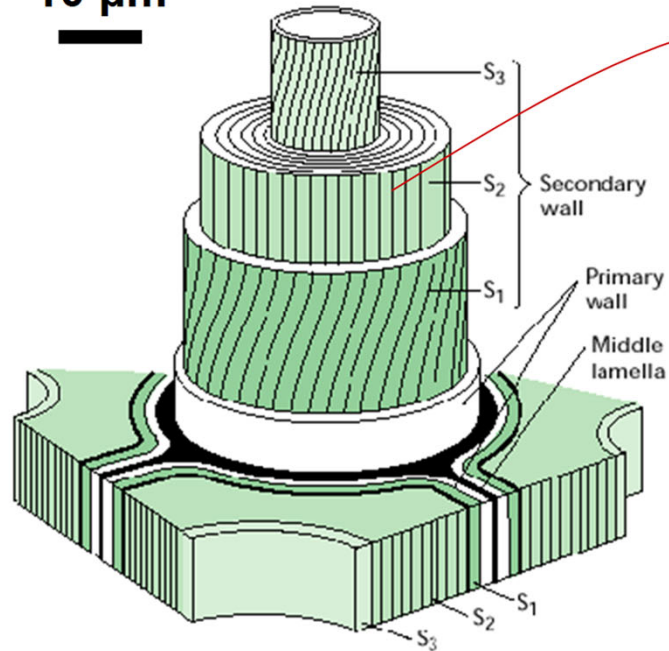


Cellulose microfibril

Diameter: 2-20 nm
(In wood: 3-4 nm)

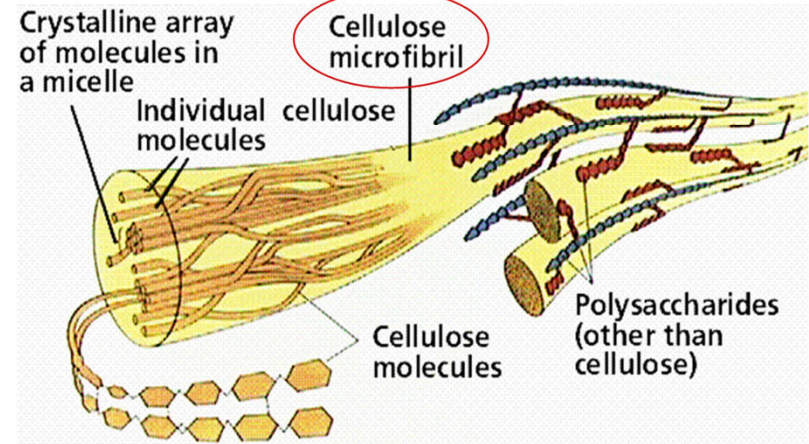

Ultrastructure: cellulose microfibrils

Aggregates: 12-20 nm
(or more)

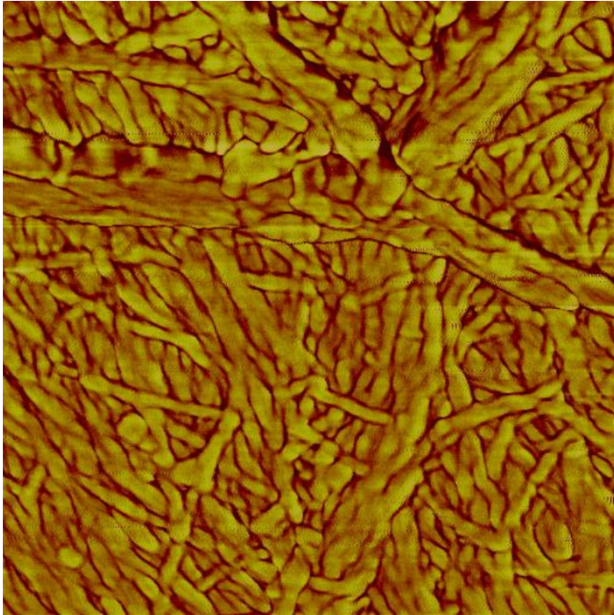

AFM image of a surface of bleached birch kraft pulp; sample untreated.

Imaged by M. Suchy 2008.

Individual microfibrils: ~3.5 nm



TEM image of longitudinal cross-section of chlorite delignified pine cell wall; freeze-dried and stained.



A. Heyn *J. Ultrastructure Res.* **1969**, 26, 52.

Cellulose nanofibres

Preparation of nanofibrillar cellulose aims at isolating the individual microfibrils (nanofibrils) from the cell wall structure.

Seminal challenges in isolation:


- tight, hierarchical structure of the plant cell wall
- inherent tendency of cellulose to aggregate

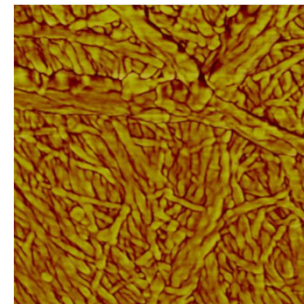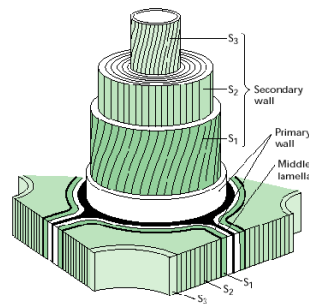

Preparation of cellulose nanofibres: mechanical disintegration

EARLY EXAMPLES OF INDIVIDUALIZATION OF MICROFIBRILS

METHOD: ULTRASONICATION

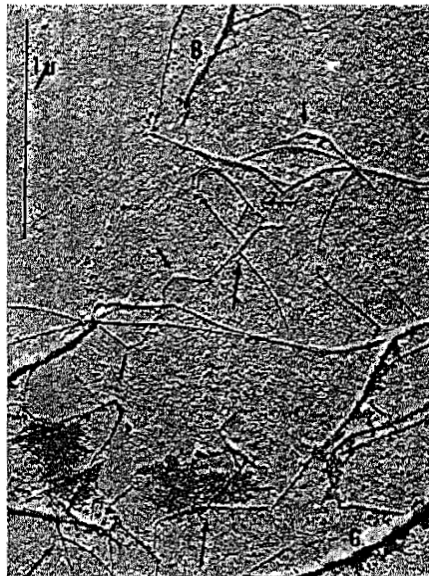

S.K. Asunmaa
Tappi **1967**, 49, 319.

From aspen holocellulose





Gardner and Blackwell
J. Polym. Sci. C
1971, 36, 327.

From valonia alga

Preparation of cellulose nanofibres: mechanical disintegration


First attempt to isolate microfibrils for materials science purposes.

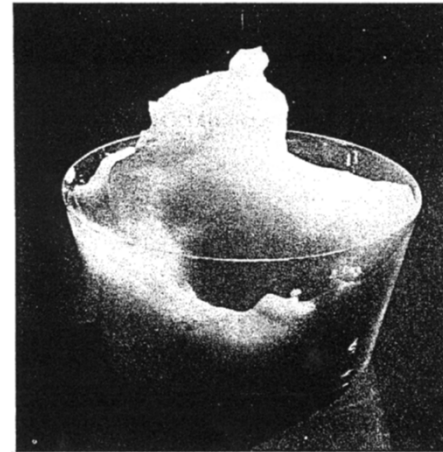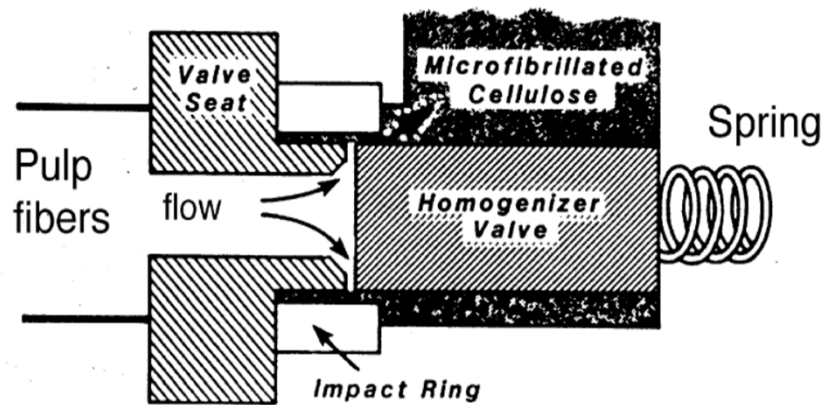

Turbak et al. *J. Appl. Polym. Sci. Appl. Polym. Symp.* 1983, 37, 815.

Preparation of cellulose nanofibres: mechanical disintegration

Enzymatic pretreatment to bleached sulphite pulp.

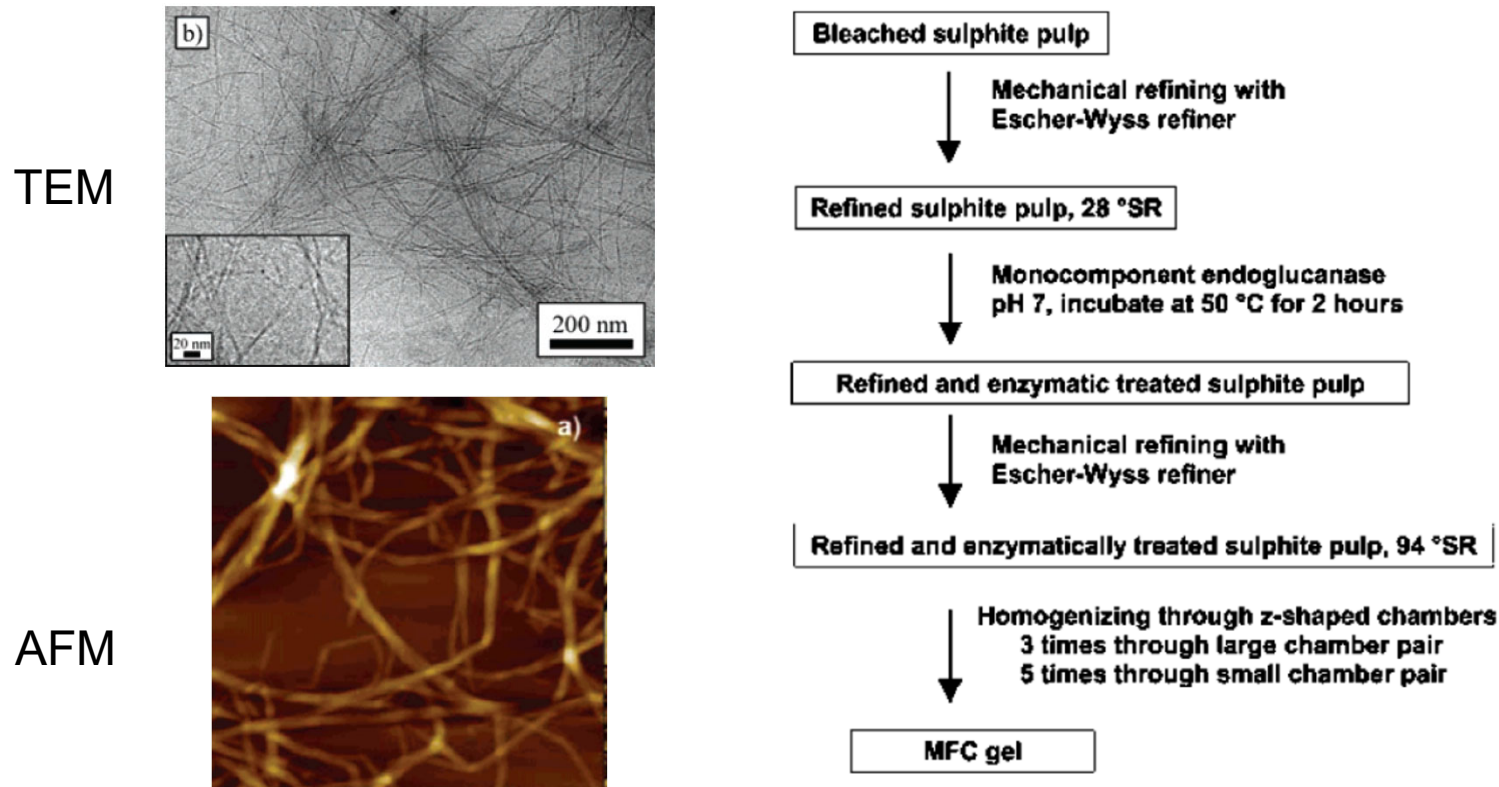


Microfibrils and microfibril aggregates, ca. 5-10 nm in size.

Pääkkö et al. *Biomacromolecules* 2007, 8, 1934.

Preparation of cellulose nanofibres: mechanical disintegration

Wood powder, delignified by chlorite, hemicellulose matrix leached out by alkaline treatment → 1 pass through Masuko grinder

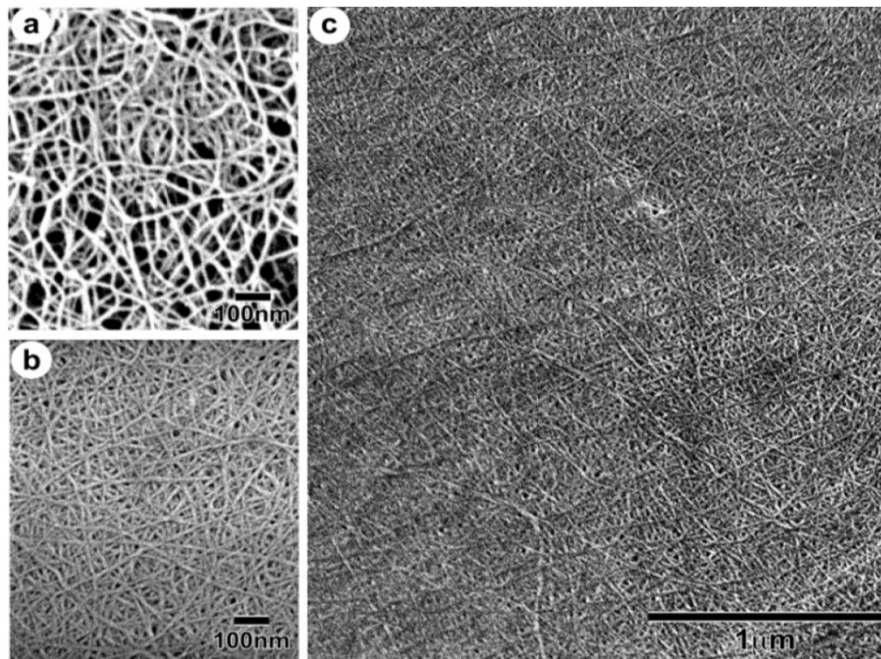


Highly monodisperse 15 nm wide microfibril aggregates

Preparation of cellulose nanofibres: chemical isolation

TEMPO-mediated oxidation

- 2,2,6,6-tetramethyl-1-piperidinyloxy radical (TEMPO) is an oxidation catalyst
- TEMPO-NaBr-NaClO –system selectively oxidized **primary alcohols** in polysaccharides, i.e., C6 position in cellulose

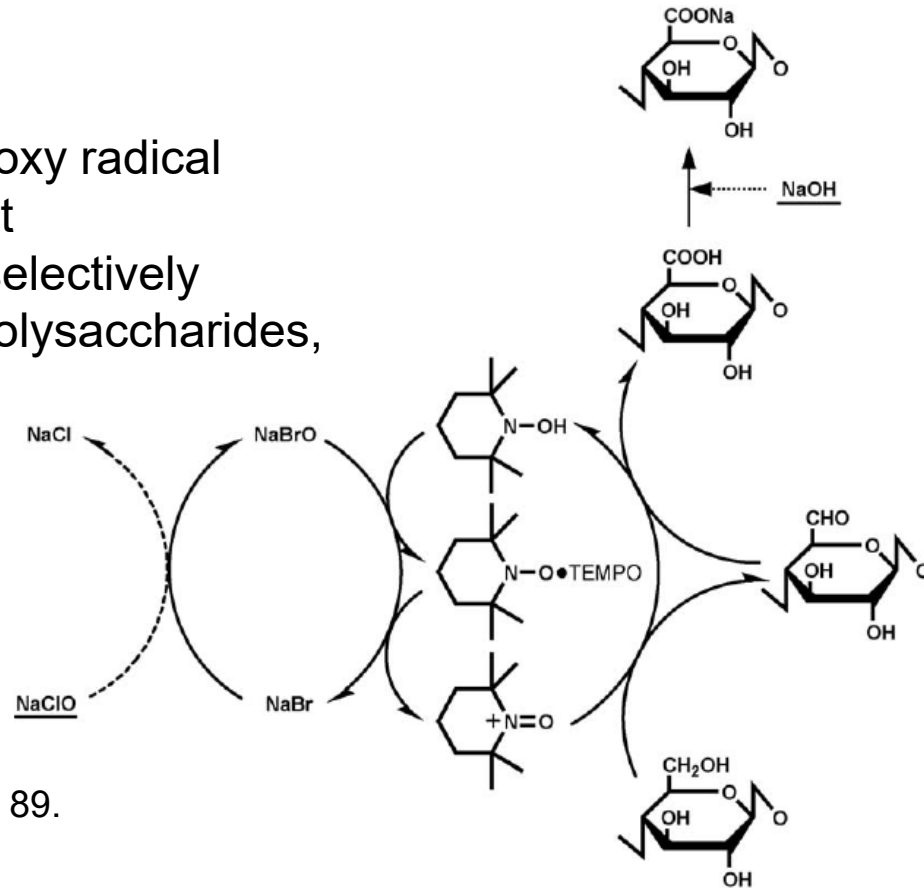

Pioneered for polysaccharides:
de Nooy et al. *Carbohydr. Res.* **1995**, 269, 89.

Pioneered for cellulose:
Isogai and Kato *Cellulose* **1998**, 5, 153.

Preparation of cellulose nanofibres: chemical isolation

TEMPO-mediated
oxidation of native fibres





Mechanical
stirring



Centrifugation




supernatant

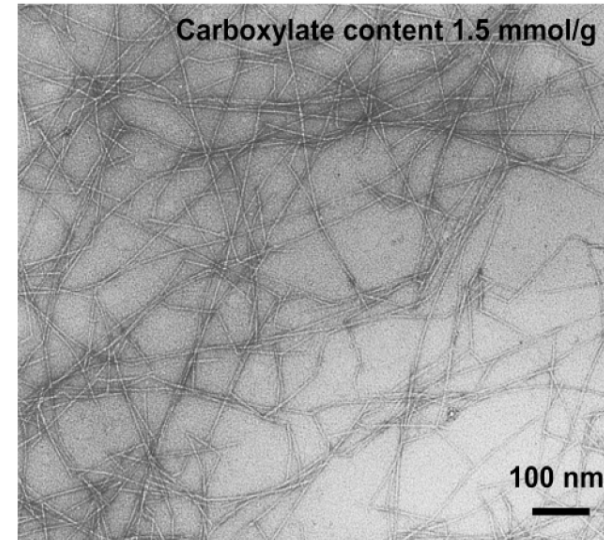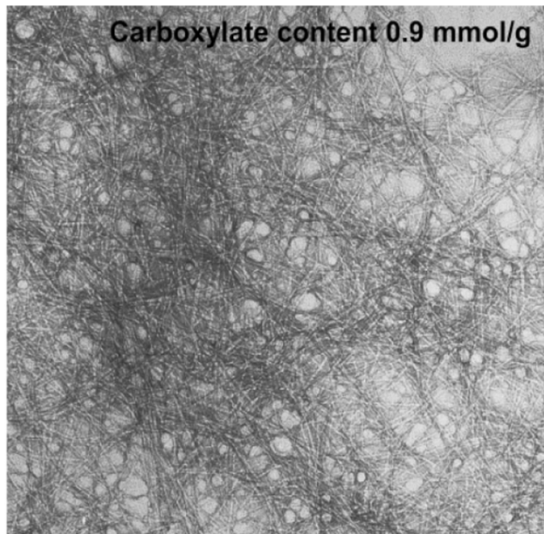

RESULT: highly monodisperse microfibrils (3-4 nm width)

Preparation of cellulose nanofibres: chemical isolation


Why do we get individual microfibrils from TEMPO-oxidation?

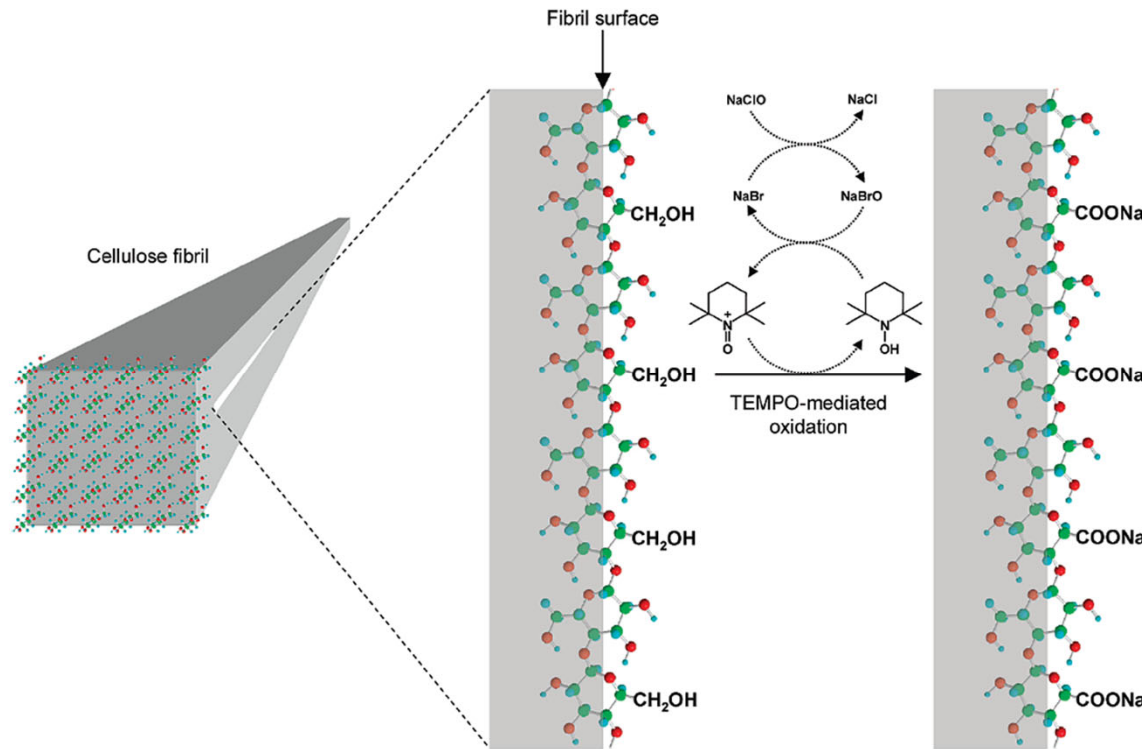

Only the surface of the microfibrils is oxidized → electrostatic repulsion.


Preparation of cellulose nanofibres: chemical isolation

Effect of starting material

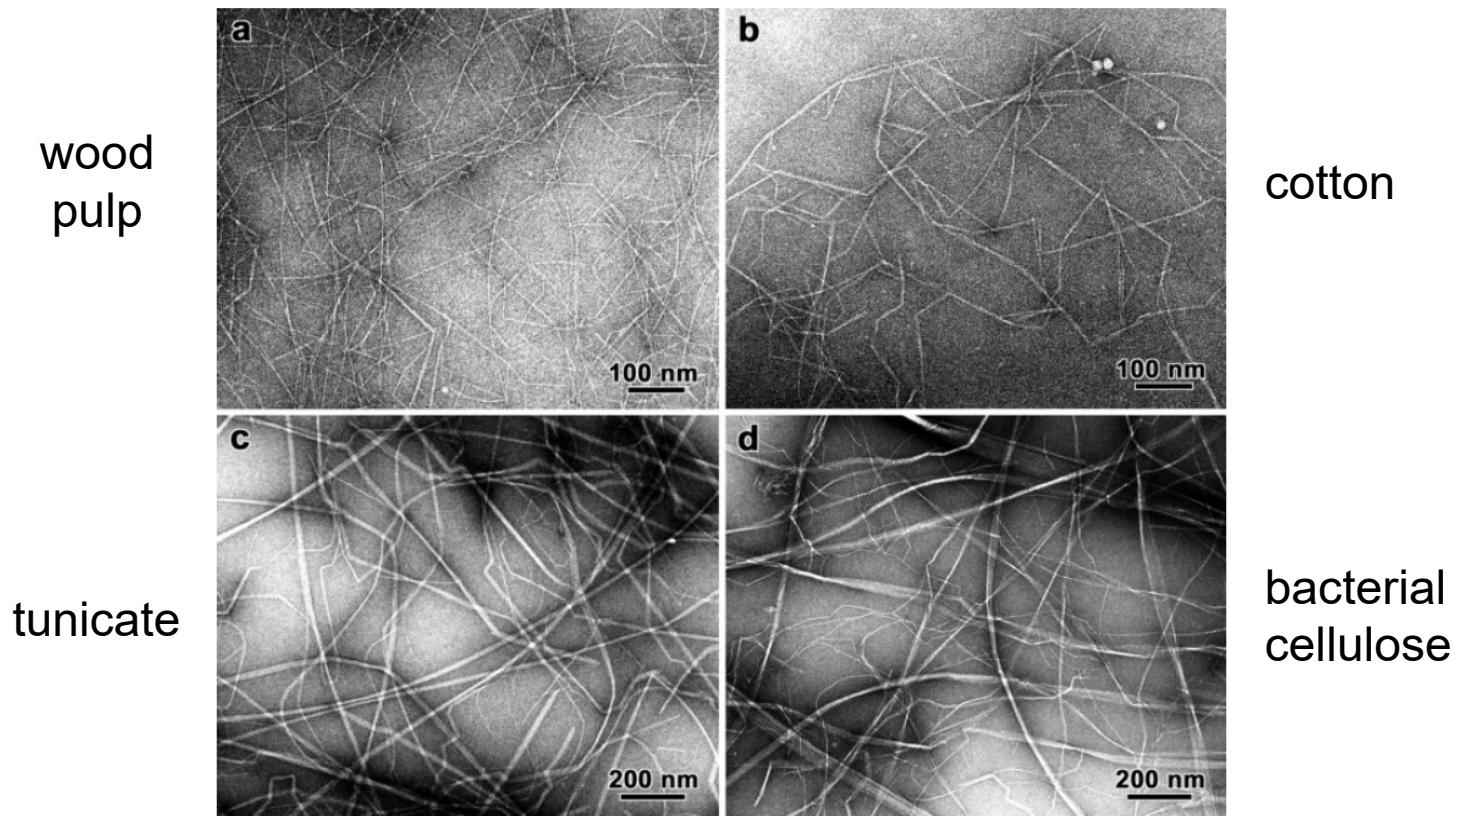

Preparation of cellulose nanofibres: chemical isolation

- TEMPO-mediated oxidation of cellulose reduces DP, especially with regenerated cellulose grades
- extensive survey on DP: Isogai et al. *Cellulose* **2009**, 16, 117.
- however, recent research points out that at neutral conditions in a TEMPO/NaClO/NaClO₂ system, the DP reduction is minimized

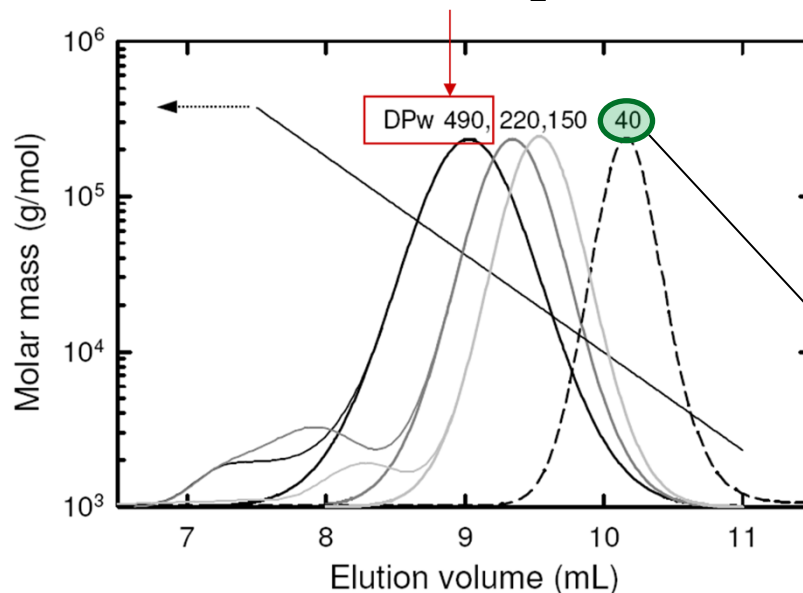


Original DP: **680**

DP after TEMPO/NaClO/NaClO₂
(oxidation for 3 days, pH 5.8): **490**

DP after TEMPO/NaBr/NaClO
(2 hours, pH 10): **40**


Preparation of cellulose nanofibres: chemical isolation

Neutral conditions (TEMPO/NaClO/NaClO₂) system result in straighter microfibrils (less defects).

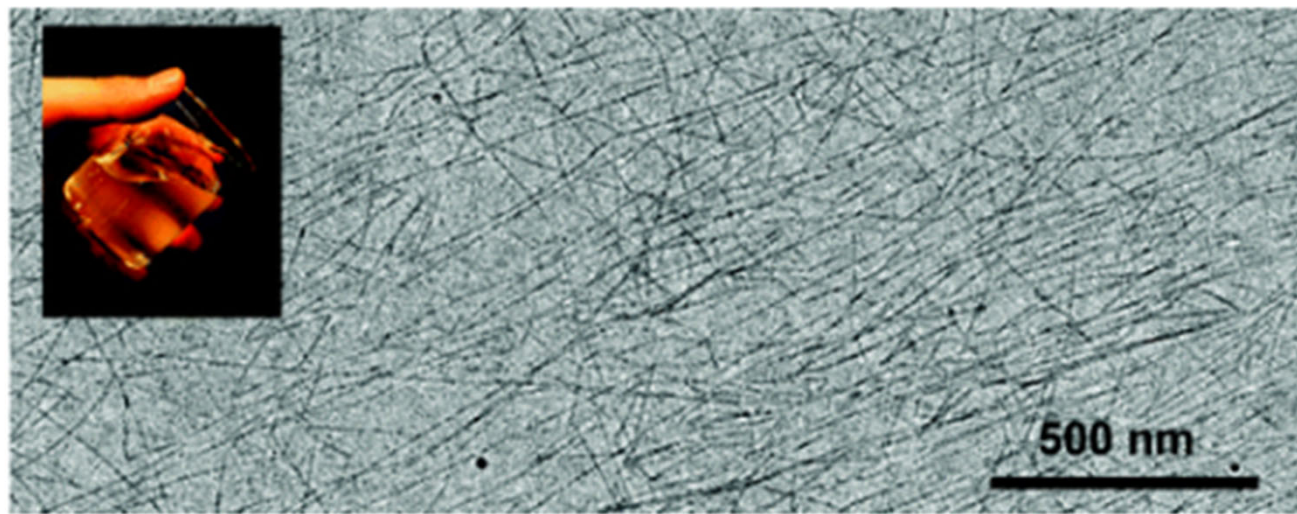

Cellulose nanofibres: bacterial cellulose


- a species of bacteria (*acetobacteria xylinum*) is able to produce pure cellulose microfibrils from sugars
- individual microfibrils are formed on spot
- macroscopically, bacterial cellulose forms a gel like many other types of nanofibrillar cellulose

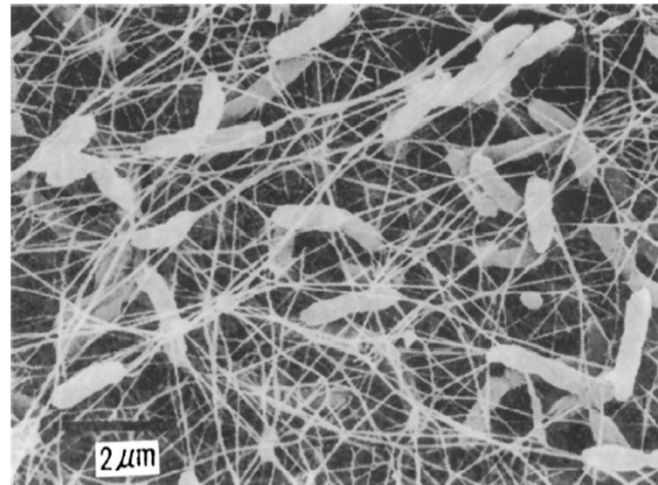


- the microfibrils from bacterial cellulose are larger than in plant cellulose: cross section $> 70\text{-}140\text{ nm} \times 7\text{ nm}$

Cellulose nanocrystals: preparation


Structure of cellulose microfibril

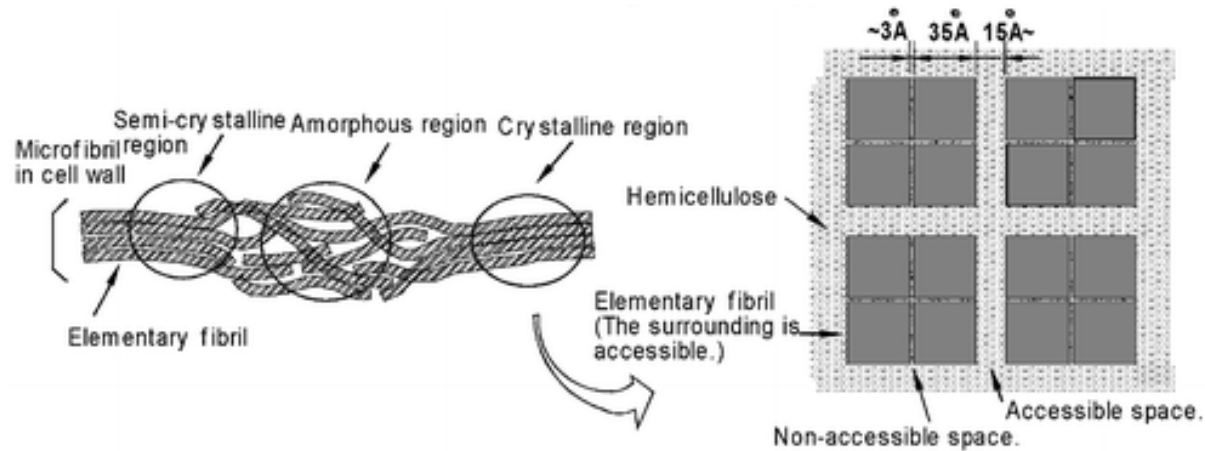


Crystallographic data presents evidence that cellulose within microfibrils is not totally crystalline.




Proposition:
cellulose runs through alternating crystalline and “amorphous” regions.

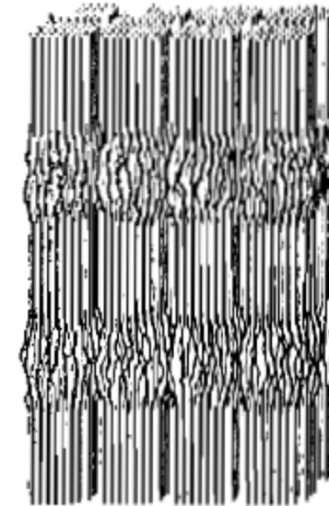

Structure of cellulose microfibril

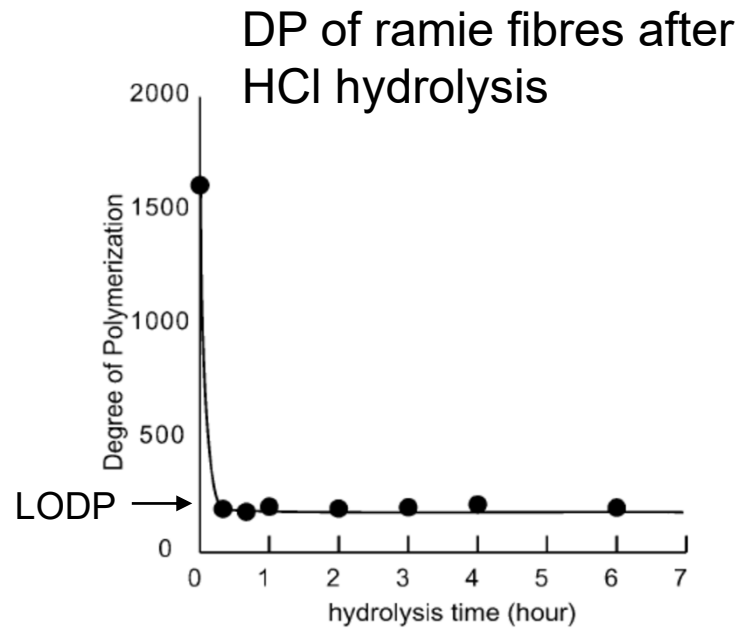

SANS* pattern of untreated ramie

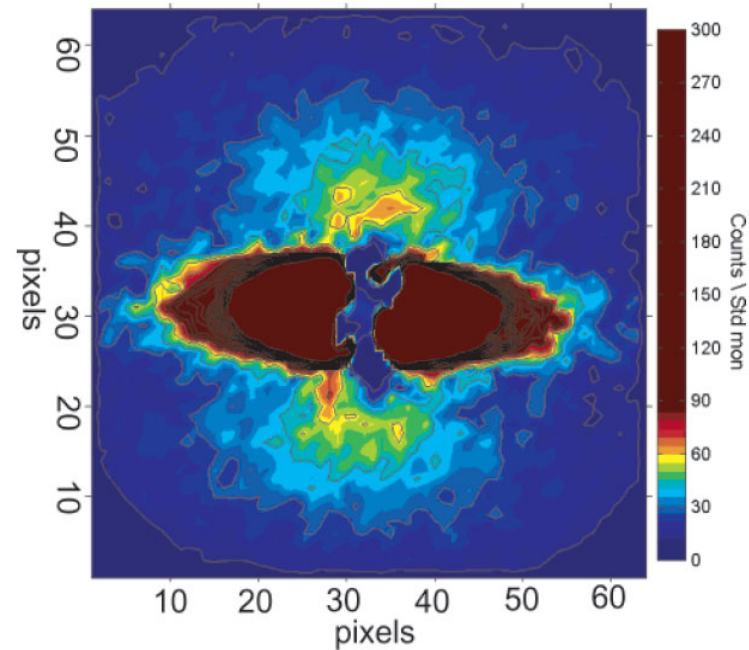


Crystallite length (i.e. length of crystalline domains) by SANS agrees with the level-off degree of polymerization (LODP).

* Small angle neutron scattering

Nishiyama et al. *Biomacromolecules* **2003**, 4, 1013.

Cellulose nanocrystals



Preparation of cellulose nanocrystals is based on the fringed fibrillar structure of the native cellulose microfibril.

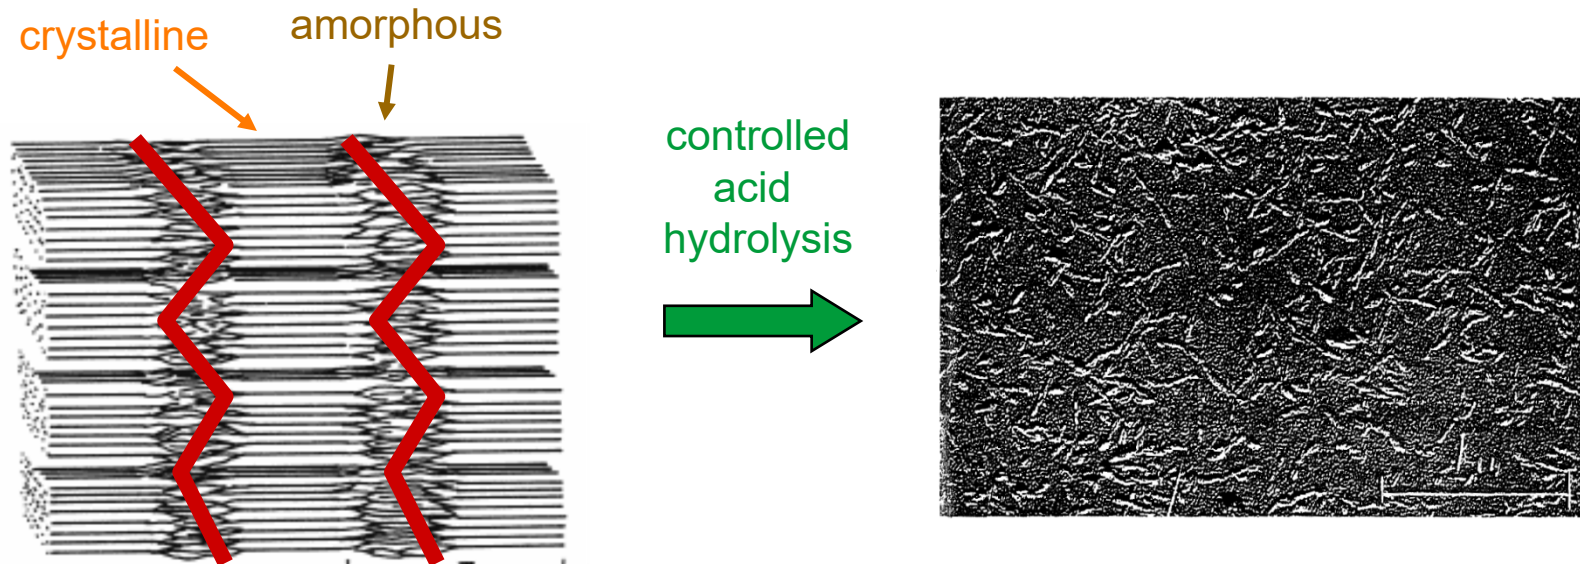

Proposition: controlled acid hydrolysis leads to disruption of amorphous domains leaving crystalline cellulose intact.


Recap: cellulose structure

- “Amorphous” regions are more like defects or dislocations between the crystallites

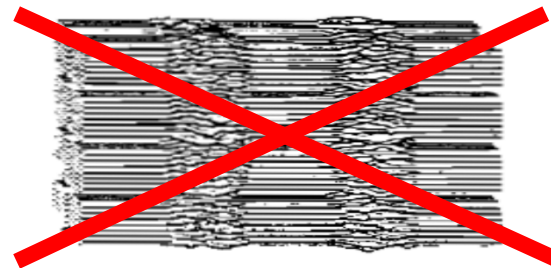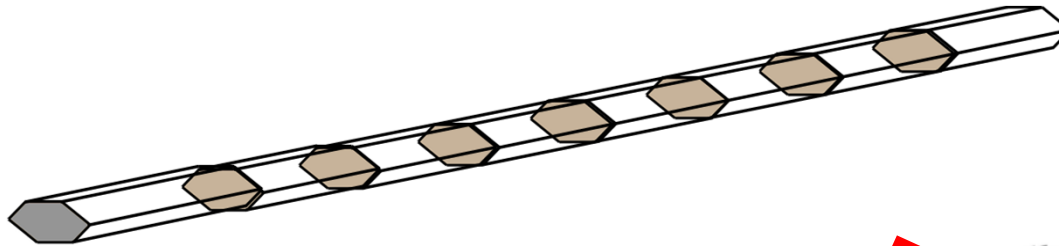


Cellulose nanocrystals - dimensions

Nanocrystal dimensions depend on the starting material (botanical source).

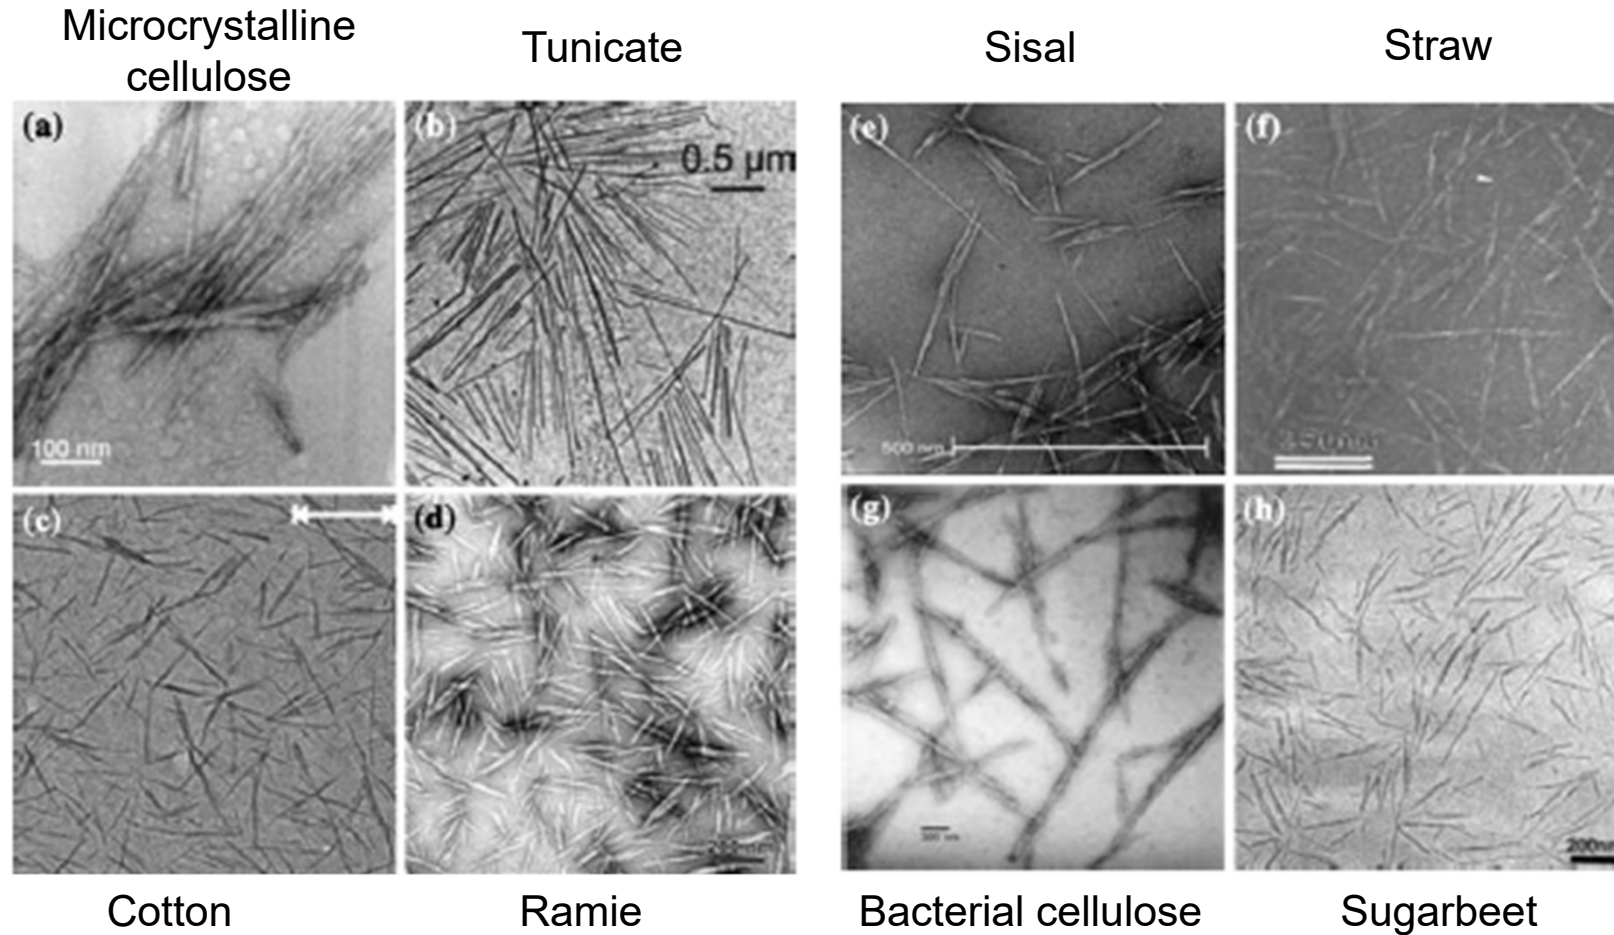

Eichhorn et al. *J. Mater. Sci.* **2010**, 45, 1.

Cellulose nanocrystals - dimensions

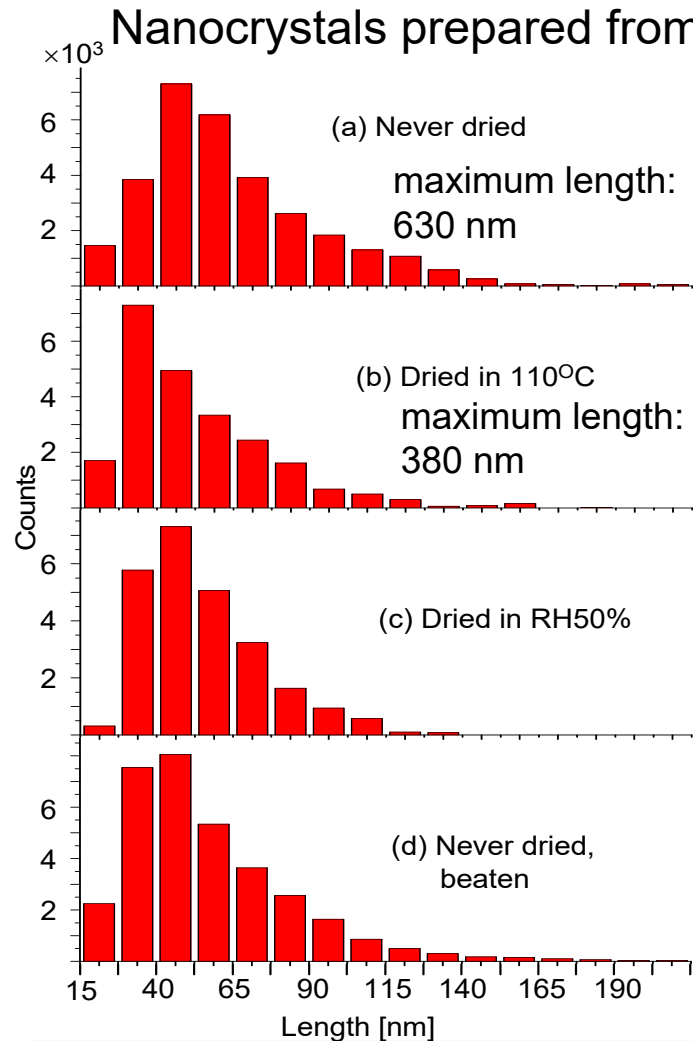


Average length is roughly similar in all samples (~60 nm)
→ corresponds to LODP of kraft pulp

- higher number of longer nanocrystals in never dried samples
- higher amount of shorter nanocrystals in dried samples



ACID HYDROLYSIS IS MORE EFFECTIVE ON DRIED FIBRES.

Cellulose nanocrystals – surface charge

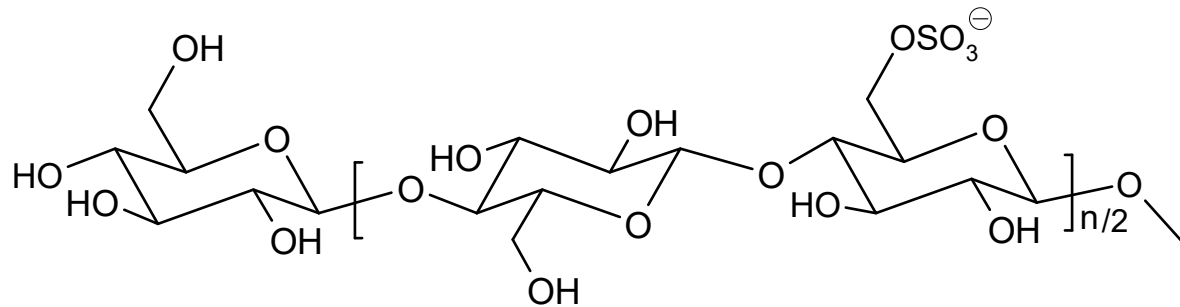

When prepared with sulfuric acid, organic sulphate groups are introduced on the surface of the nanorods.




electrostatic repulsion


STABLE SUSPENSION IN WATER

Cellulose nanocrystals – liquid crystals


Cellulose nanocrystals spontaneously forms a liquid crystal phase in solution.

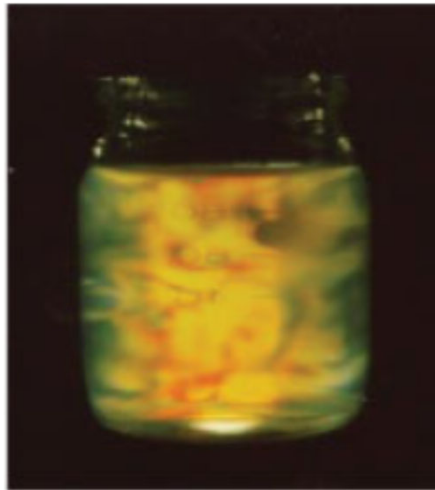

Photograph of rodlike nanocrystals in aqueous suspension. The liquid crystal phase has been formed.

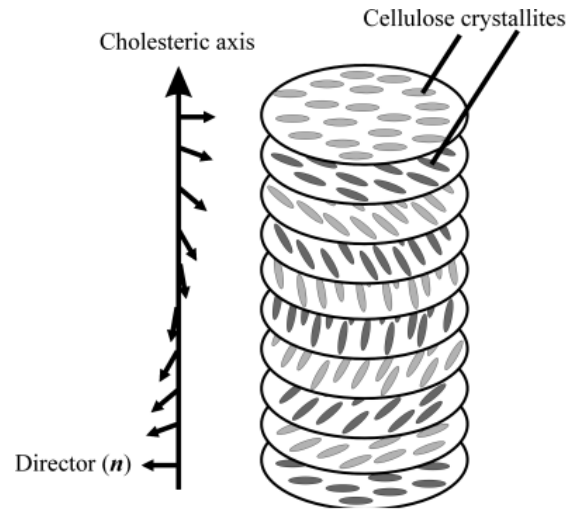


chiral nematic phase formed by cellulose crystallites

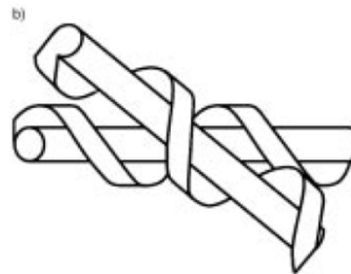

tight packing by the chiral interaction of screwlike rods

Cellulose nanocrystals – new preparation method with acid vapour

Concept for preparation of cellulose nanocrystals with acid vapor

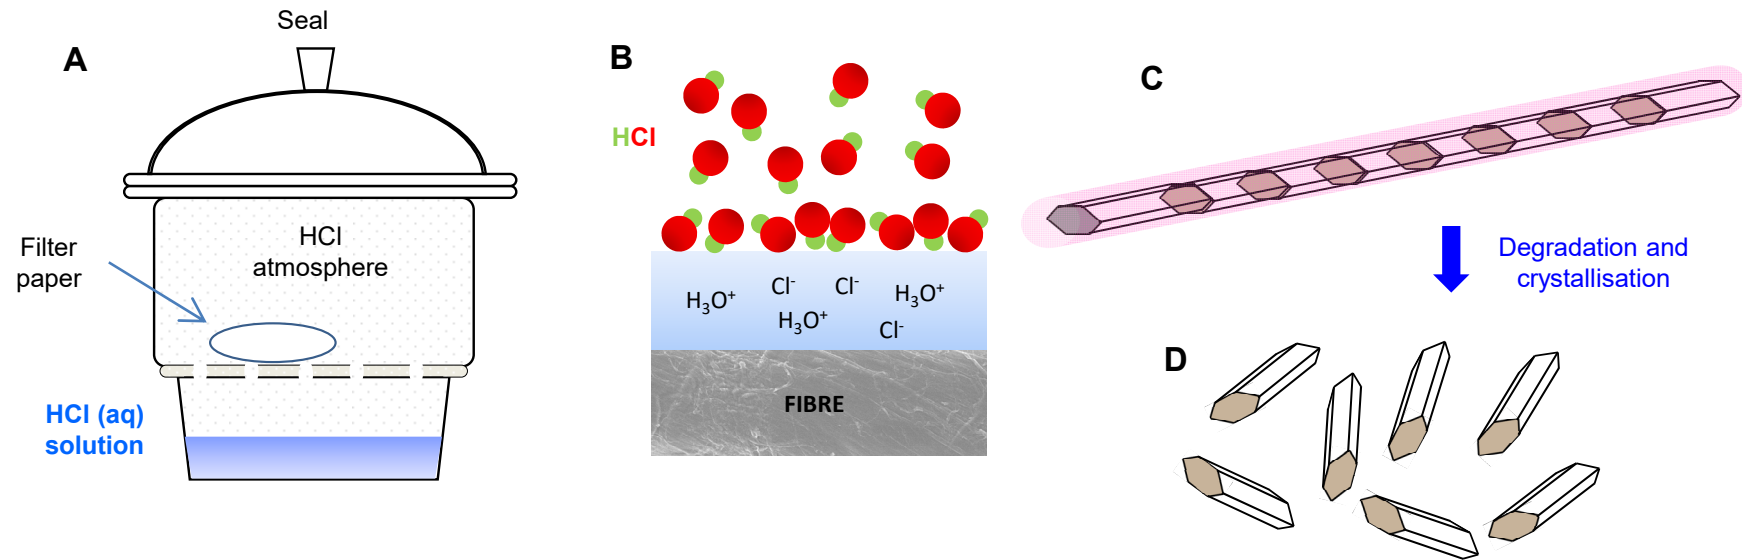


- Hydrogen chloride (HCl) vapor adsorbs on fibre surface
- Fibre surface is always covered by water in ambient conditions
 - HCl dissociates in water, i.e., it becomes an acid
 - Acid and water degrade cellulose until the LODP
 - Nanocrystals can be isolated from the hydrolysed fibres

Angew. Chem. Int. Ed. **2016**, *55*, 14455.

Degradation of cellulose by HCl vapour

Cotton linter fibres (Whatman 1 filter paper)

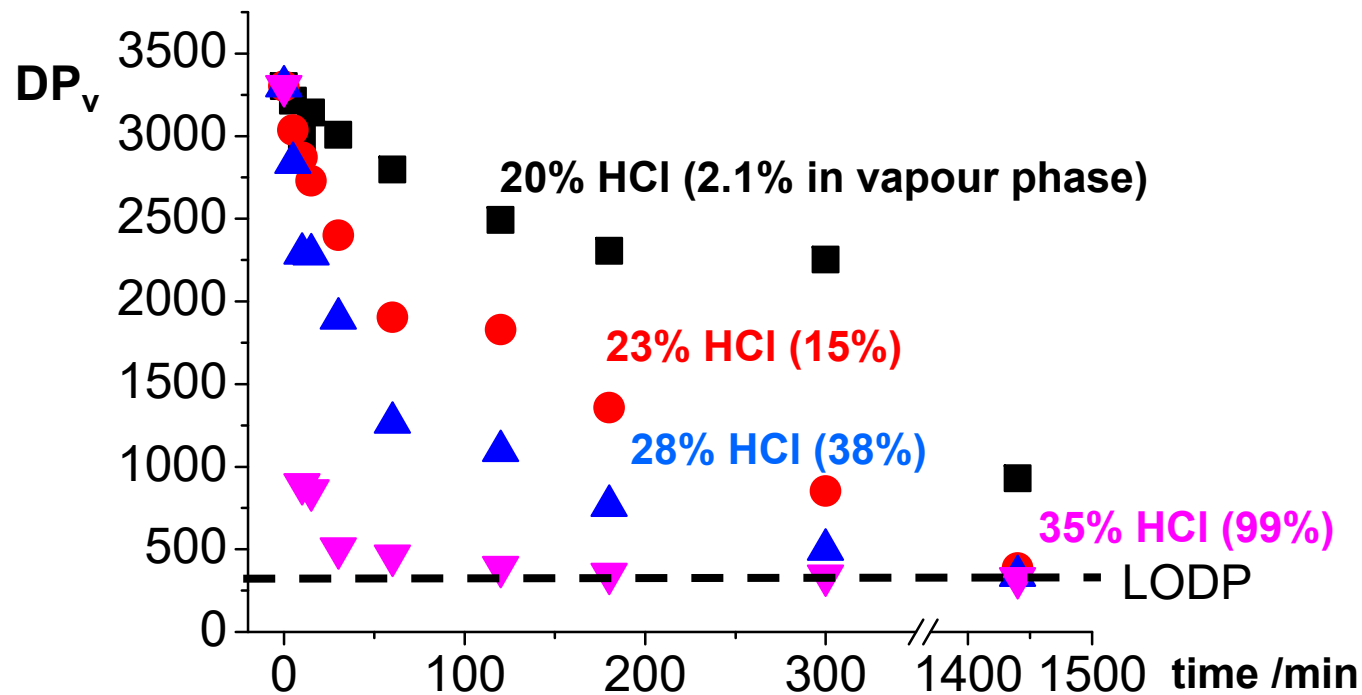


→ Rapid degradation down to LODP level **at room temperature**

HCl accumulation on fibres

Because HCl resides originally in vapour phase, it must reach the fibres by adsorption

Fibres are always covered by a thin layer of water (3-5%)

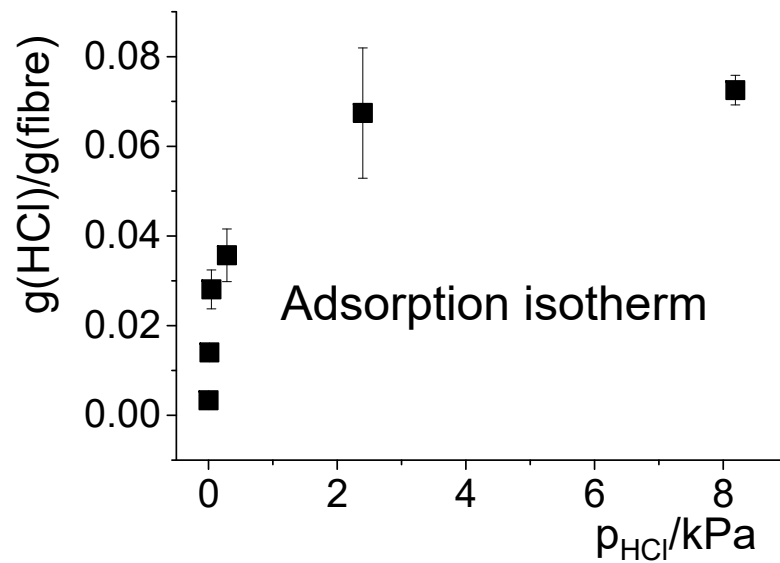

Practical CNC preparation with HCl vapour

Hydrolysis with HCl vapour:
35% HCl, 4 h, room temperature




Grinding the hydrolysed
substrate in a Wiley mill




Dispersing the powder
in formic acid (heavy sonication)

Note: hydrolysis with HCl(g) is easy,
dispersion of CNCs is difficult

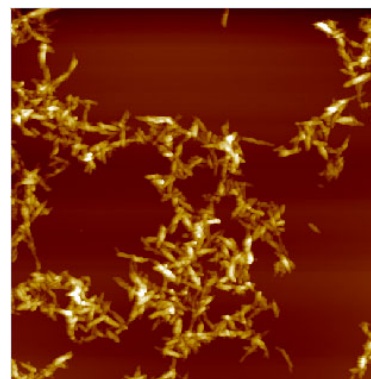


5×5 μm²

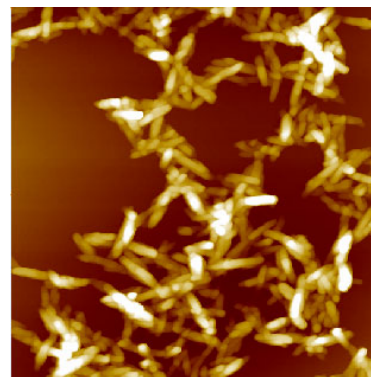

2×2 μm²

CNC dispersion from hydrolysed fibres


- Different dispersion methods trialled for HCl (g) hydrolysed CNCs

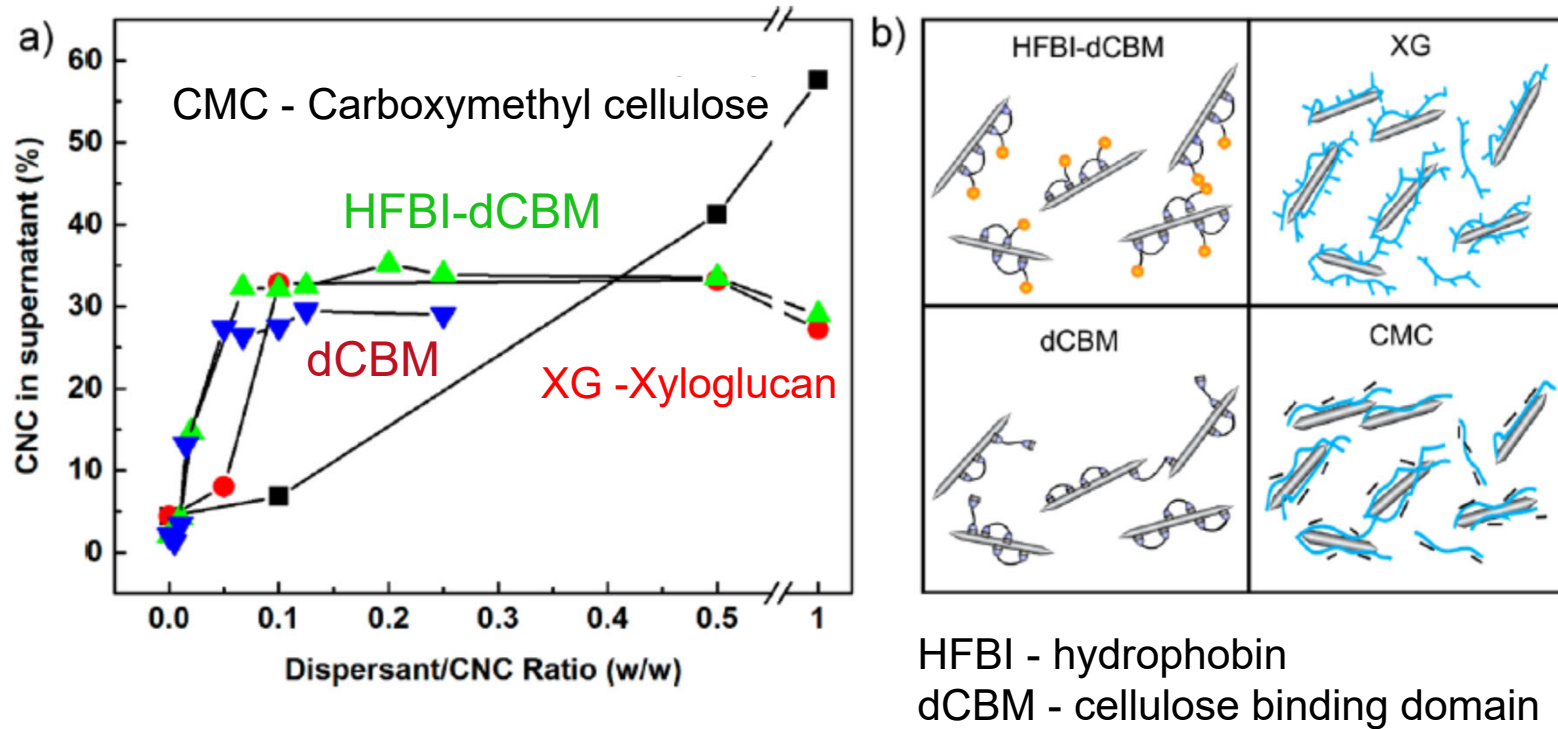

- Carboxymethyl cellulose works reasonably well for dispersing the CNC from fibres that have been hydrolysed with HCl vapour

Fang et al. *Biomacromolecules* **2016**, *17*, 1458.

CNCs by acid gas and TEMPO-oxidation

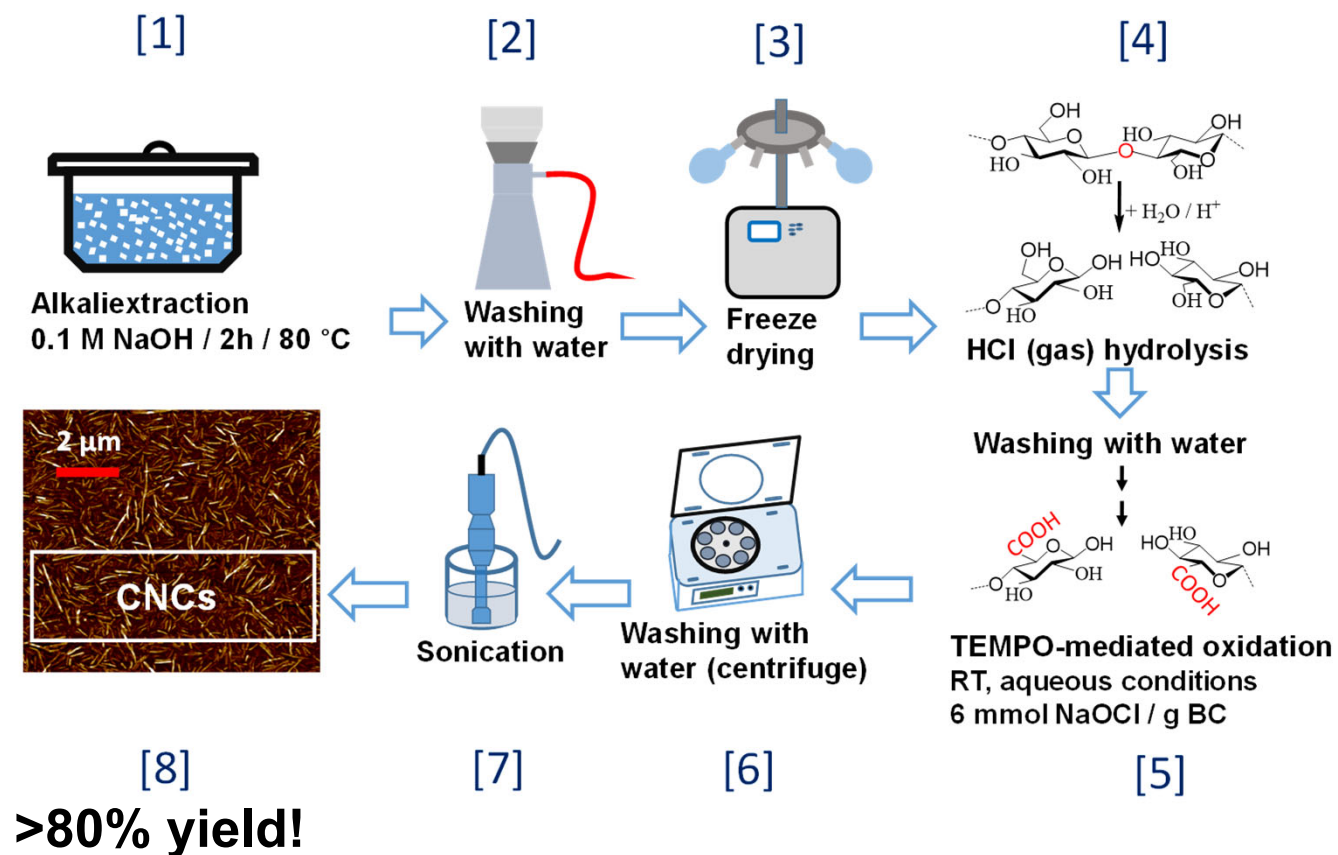


Cellulose nanofibres: modifications

Strategies for CNF modification

- CNF modification is *a/ways* surface modification
- Functional groups are attached on the surface of CNF and the interior semi-crystalline microfibril remains intact
- CNF modification can be performed either before CNF preparation (pre-treatment) or after the CNF has been isolated



Carboxymethylation of CNF

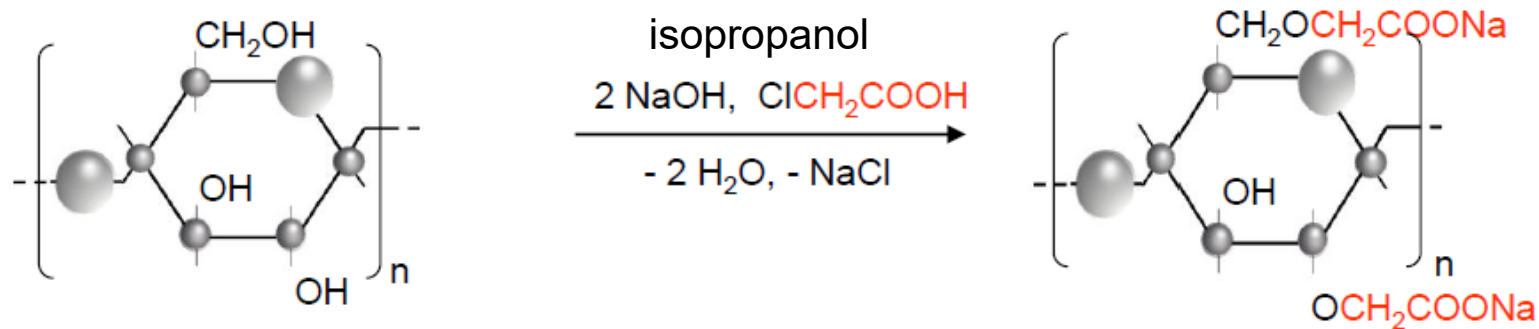

- Carboxymethylation is performed on dissolving pulp prior to CNF preparation (mechanical isolation of CNF)
- Additional carboxymethyl units on CNF surface result in highly charged CNF

Acetylation of CNF

CNF is acetylated in dimethyl formamide (DMF) with a pyridine catalyst

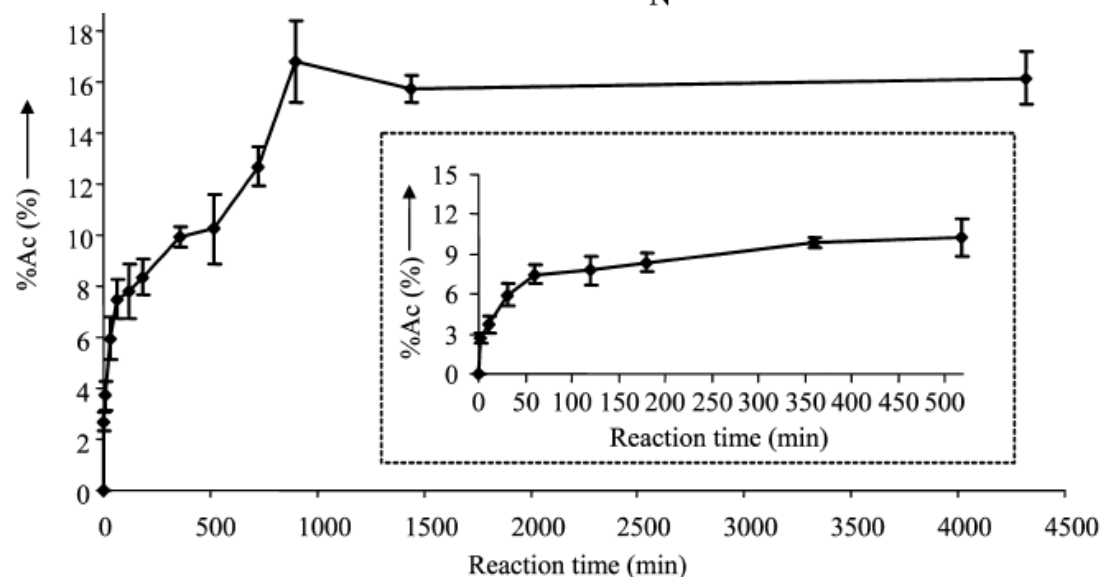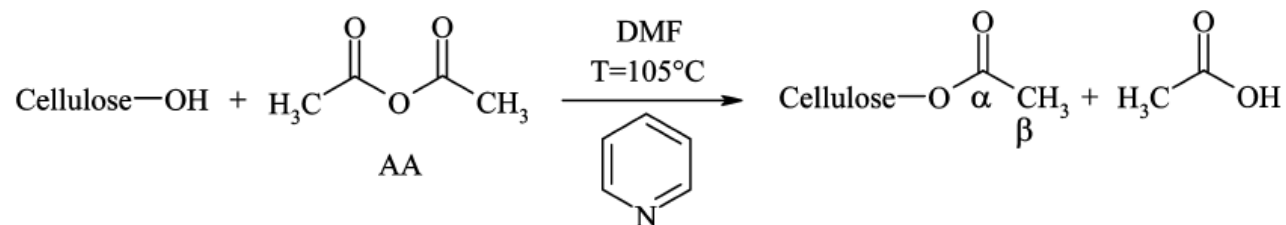


Acetyl content can be easily tuned with reaction time.

Tingaut et al. *Biomacromolecules* 2010, 11, 454.

Acetylation of CNF

Acetyl content

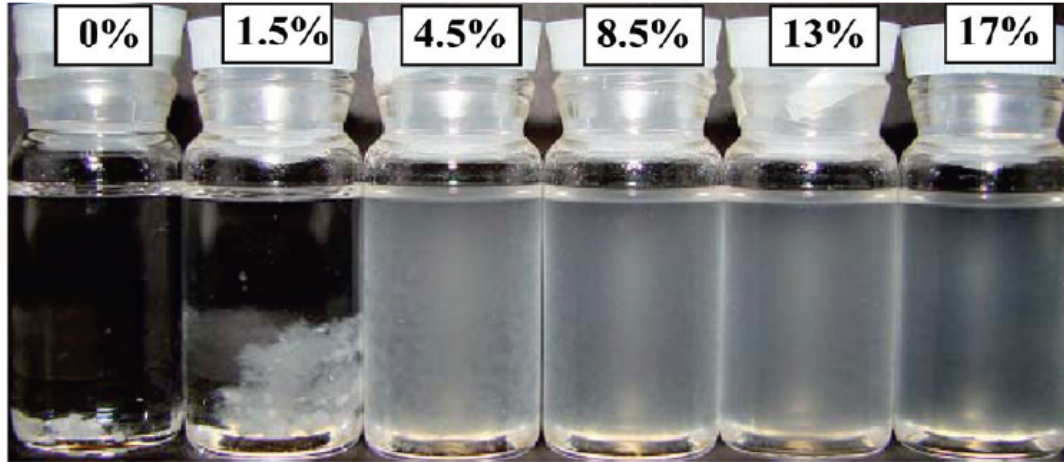

- Acetylation dramatically improves the dispersibility of NFC in chloroform

Cellulose nanocrystals: modification


General issues on CNC modifications

- Like NFC, CNC modification aims at surface functionalization, leaving the crystalline core intact
- Because of the sulphate groups on the CNC surface, they disperse extremely well in water
- However, water is a tricky medium for organic synthesis: most reactions will not work
- Nearly all CNC modification methods are designed to occur after the CNC preparation (no pre-treatments because of harsh preparation conditions)
- Grafting of polymer chains on CNC surface is particularly popular at present

Cellulose nanocrystals – dispersions

Problem with cellulose nanocrystals:

- they disperse almost only in water (if charged with sulphate groups)
 - they do not disperse in nearly anything if they are not charged
- the use in hydrophobic composite matrix is difficult (aggregation)

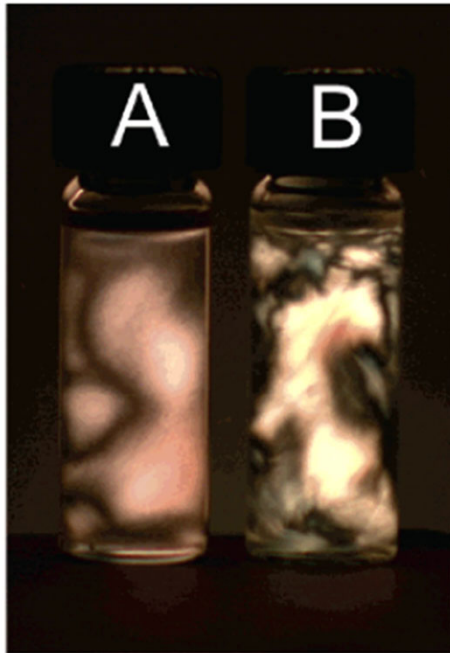


Notable exceptions with dispersing solvents:

- m-cresol (A)
- formic acid (B)

Otherwise, there are intensive research efforts to chemically modify CNCs to improve their dispersion in various media.

van den Berg et al. *Biomacromolecules* **2007**, 8, 1353.

CNC modification routes

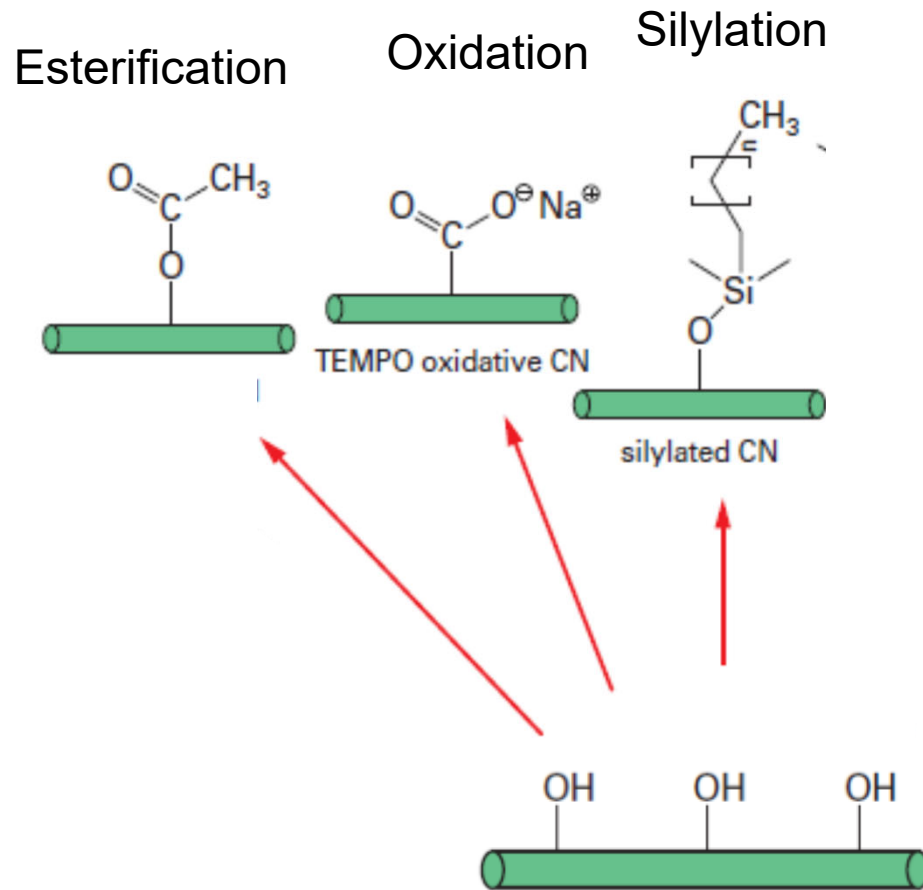

Note:
Etherification is not
generally considered
for already isolated
CNCs


Polymer grafting on CNCs

Polymer grafting onto nanocrystal surface is particularly trendy.

TEMPO-oxidation on whisker surface



Attachment of poly(styrene) or poly(tert-butyl acrylate) on whisker surface (*grafting-to*)

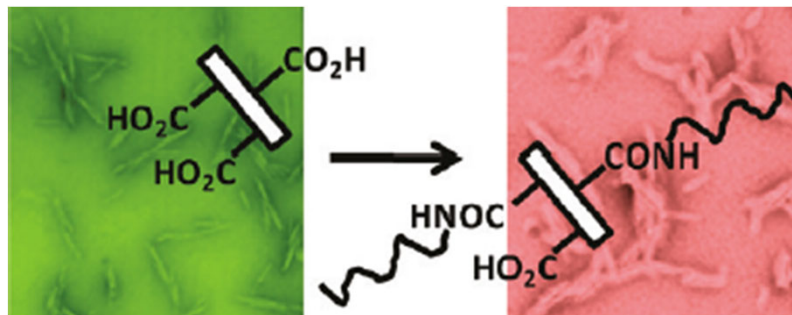

Harrison et al. *Biomacromolecules* 2011, 12, 1214.


Polymer grafting on CNCs

Polymer grafting onto nanocrystal surface is particularly trendy.

Activation of nanocrystal surface with an initiator

→ atom transfer radical polymerization (ATRP) of poly(*tert*-butyl acrylate)
(grafting-from)

→ acid hydrolysis to polyacrylic acid

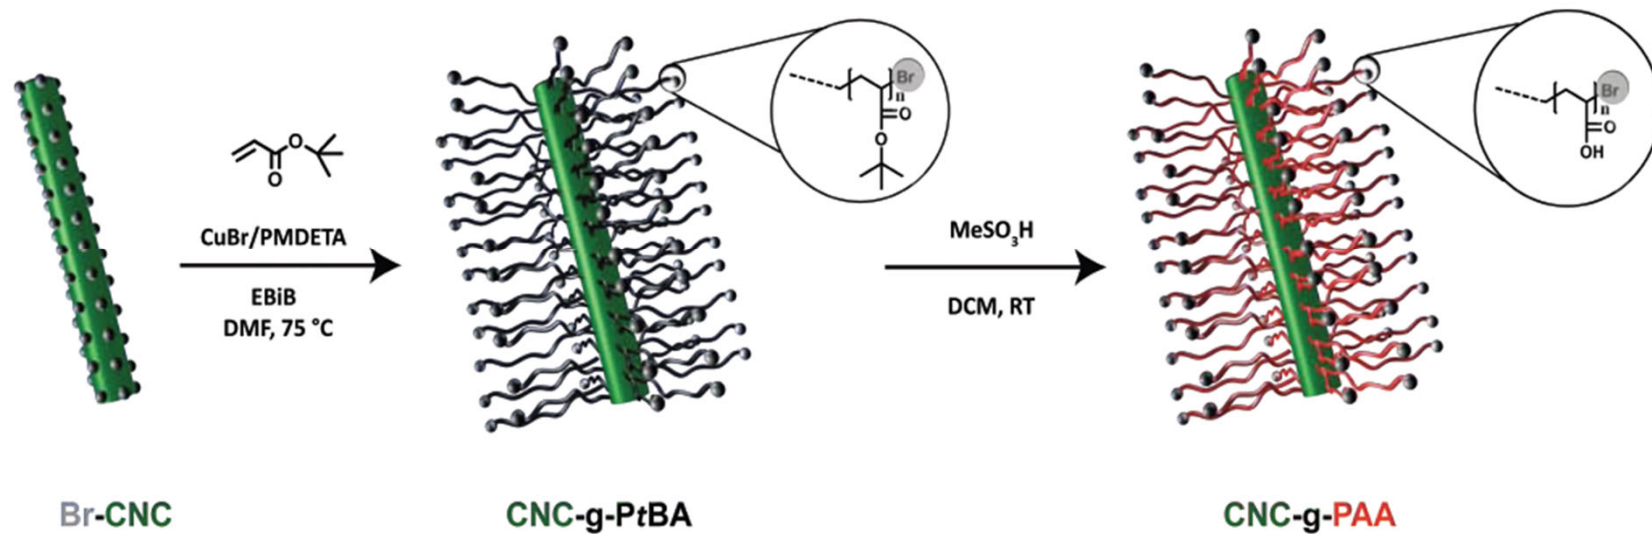

Summary: Nanofibrillar vs. nanocrystalline (CNF vs. CNC)

Different types of nanocellulose

– a comparison

Mechanically produced CNFs

- Cheap(ish) (after suitable pretreatments)
- Polydisperse width, mostly higher than in native microfibrils
- Not very stable in dispersion
- Always present with hemicellulose (anything between 3-25%) and traces of lignin

Chemically produced CNFs (TEMPO-oxidized)

- Sodium hypochlorite is expensive
- Monodisperse width that corresponds to the native microfibril
- Stable dispersion because of the charged COOH-groups on the surface
- Not pure cellulose but uronic acid groups on the nanofibril surface
- Includes also hemicellulose which is difficult to quantify because these CNFs resist acid hydrolysis

Different types of nanocellulose

– a comparison

Cellulose nanofibres

- **Gels at low concentrations (0.5-1.5 w%)**
- Very high aspect ratio (l/d can be ~1000)
- Flexible, spaghetti-like shape
- Behaviour not always well defined
- Intensive research from 2007 onwards
- Promising in especially composites applications (reinforcing phase)

Cellulose nanocrystals

- **Fluid dispersion at low concentrations**
- Not very high aspect ratio
- Rod-like: always straight shape
- Intensive research from 1992 onwards (although a surge after 2005 occurred)
- Promising as filler material, viscosity controller etc.
- Many high end applications have been proposed (incl. liquid crystal utilization)

Recommended review articles

On all kinds of nanocellulose :

Klemm et al. *Angew. Chem. Int. Ed.* **2011**, 50, 5438.

Kontturi et al. *Adv. Mater.* **2018**, 32, 1703779.

Ajdary et al. *Adv. Mater.* **2020**, 34, 2001085

On cellulose nanofibres:

Nechyporchuk et al. *Ind. Crops Prod.* **2016**, 93, 2.

Wang et al. *Biomacromolecules* **2021**, 22, 4037.

On cellulose nanocrystals:

Habibi et al. *Chem. Rev.* **2010**, 110, 3479.

Mariano et al. *J. Polym. Sci., Part B* **2014**, 52, 791.

Trache et al. *Nanoscale* **2017**, 9, 1763.

On bacterial cellulose:

Wang et al. *Carbohydr. Polym.* **2019**, 219, 63.

On nanocellulose modification:

Habibi *Chem. Soc. Rev.* **2014**, 43, 1519.

Eyley and Thielemans *Nanoscale* **2014**, 6, 7764.